

Accepted Manuscript

Rapid sensing of melamine in milk by interference green synthesis of silver nanoparticles

S. Varun, S.C.G. Kiruba Daniel, Sai Siva Gorthi


PII: S0928-4931(16)31847-1
DOI: doi: [10.1016/j.msec.2016.12.011](https://doi.org/10.1016/j.msec.2016.12.011)
Reference: MSC 7203

To appear in: *Materials Science & Engineering C*

Received date: 20 October 2016
Revised date: 22 November 2016
Accepted date: 4 December 2016

Please cite this article as: S. Varun, S.C.G. Kiruba Daniel, Sai Siva Gorthi , Rapid sensing of melamine in milk by interference green synthesis of silver nanoparticles. The address for the corresponding author was captured as affiliation for all authors. Please check if appropriate. Msc(2016), doi: [10.1016/j.msec.2016.12.011](https://doi.org/10.1016/j.msec.2016.12.011)

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

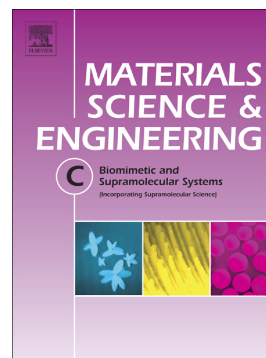

Rapid sensing of melamine in milk by interference green synthesis of silver nanoparticles

Varun S, S.C.G. Kiruba Daniel, Sai Siva Gorthi *

*Department of Instrumentation and Applied Physics, Indian Institute of Science (IISc),
Bangalore, Karnataka, India, 560012*

Tel: +91 80 2293 3529, E-mail: saisiva.gorthi@iap.iisc.ernet.in

ABSTRACT

A highly sensitive, selective, and rapid interference green synthesis based determination of potential milk adulterant melamine has been reported here. Melamine is a nitrogenous compound added to milk for mimicking proteins, consumption of which leads to kidney stones and renal failures. Melamine interacts with ascorbic acid (AA) through strong hydrogen-bonding interactions, thus resulting in an interference/interruption in the formation of silver (Ag) nanoparticles which was confirmed by UV-Vis spectroscopy and Transmission Electron Microscopy (TEM). The corresponding benchmark validations for melamine spiked milk samples were performed using High Performance Liquid Chromatography (HPLC). This interference in the formation of Ag nanoparticles resulted in color change that varies with concentration of melamine, thereby enabling in-situ rapid sensing of melamine from milk to a lower limit of 0.1 ppm with a linear correlation coefficient of 0.9908.

Keywords: Melamine, Interference sensing, Biosensor, Ascorbic acid, Green synthesis

1. Introduction

Food adulteration has become a serious concern in recent years. Increased awareness of health benefits as well as the consequences of bad health within the global populous has lead researchers to direct their attention towards developing portable detection techniques [1–3], for monitoring food quality. Among the various concerns of present day society, milk adulteration is

perhaps the most widespread. Different kinds of adulterants are being added to milk and dairy products on a daily basis worldwide. The adulteration of one of the most basic staples poses a significant and direct threat towards healthy sustainable living envisioned by the general population. Adulteration of milk affects the quality of milk and can even make it hazardous to consume.

Out of the identified milk adulterants, melamine (1,3,5-Triazine-2,4,6-triamine), has been known to be added to milk in order to give an incorrect high readout of apparent protein content levels due to its high nitrogen content [4] and is associated with kidney stones and renal failures in mammals [5–7]. In 2008, the Chinese milk scandal led to the death of 6 infants and a total of 300,000 babies were reported to fall ill due to the consumption of milk products adulterated with melamine [8]. The current melamine detection methods include high-end sophisticated instruments such as Gas Chromatography (GC-MS) [9], Liquid Chromatography Mass Spectroscopy (LC-MS) [10] and High Performance Liquid Chromatography (HPLC) [11]. Due to their sheer size and complex handling, these instruments and methods are out of the reach of distributors and consumers. A point-of-care, in-situ sensing mechanism that can deliver rapid and timely analysis of milk purity, is the need of the hour.

Nanotechnology has long been touted as the next level of technological evolution and in the last few decades, glimpses of its vast potential have been witnessed in various fields such as catalysis [12,13], fuel cells [14], lithium ion batteries [15,16] etc. With nanotechnology taking the forefront [17,18], there has been gradual but significant development in the fabrication of miniaturized devices for sensing of melamine and other milk adulterants using various metal plasmonic nanoparticles such as silver (Ag) [19–22] and gold (Au) [23–26]. For instance, Kaleeswaran *et al.* [15] studied the aggregation induced recognition of Ag nanoparticles by

sodium D-gluconate for sensing of melamine and the time required for synthesis/sensing was reported to be more than 2 hours with an average particle size around 12-14 nm. Another study by Ni *et al* [18] using gold nanoparticles reported an improved peroxidase-like activity of bare Au nanoparticles for visual detection of melamine with a detection limit of 0.5 μM in milk and the time required for synthesis/sensing was reported to be approximately 30 minutes with an average particle size of 10 nm. Recently, Atar *et al* proposed a novel voltametric sensor based on carbon nitride nanotubes for estimation of melamine with a detection limit of 1.0×10^{-11} M [27].

In all the above cases, the principle of sensing primarily relies on the pre-synthesized nanoparticles followed by the modification/functionalization and aggregation of previously synthesized nanoparticles due to the presence of analyte (melamine), which is a time consuming process. The development of a simple, low-cost and rapid detection technique for melamine which can be used even by an inexperienced or unskilled personnel, by realization of a portable device is highly desirable. Through this paper, a rapid way of determining melamine by means of interference green synthesis of silver nanoparticles utilizing ascorbic acid as reducing agent is reported.

2. Experimental

2.1 Materials

Silver nitrate (Merck), Ascorbic acid (S D Fine-Chem Limited), Sodium hydroxide pellets (S D Fine-Chem Limited) and Melamine (Thomas Baker) were used as received without further purification. Stock solutions were made and kept in amber colored bottles to limit the amount and spectral range of light which enters the bottle thereby eliminating any chance of photochemical reactions. Ultrapure water obtained using an ultrafiltration system (Milli-Q,

Millipore) with a measured resistivity above 18 M Ω cm at 25°C was used throughout for all the experiments.

2.2 Preparation of melamine sensor and its characterization

1 mM silver nitrate was used as a precursor [28] and 10 mM ascorbic acid (AA) as reducing agent. The particular concentration of AA was chosen on the basis of optimization experiments performed using different concentrations of AA for the synthesis of Ag nanoparticles (Fig. S3). 200 μ L of different analyte concentrations were added to 500 μ L of the silver nitrate precursor solution. 10 μ L of the AA was added to the above solution. 10 μ L of 0.85 M NaOH was added to all the microtubes for maintaining the pH of solution. The nanoparticle solutions with different concentrations of melamine were analyzed using UV-Vis absorption spectroscopy scan from 275 nm to 800 nm using the DeNovix microvolume spectrophotometer (FX 100, USA). The melamine was spiked according to the standard addition procedure followed by the milk distributors [22,29]. The pre-processed milk was prepared using 30% trichloroacetic acid and 3 M NaOH. The different concentrations of melamine spiked milk were validated using High Pressure Liquid Chromatography (Thermo Finnigan Surveyor HPLC, USA). Transmission Electron micrographs (TEM) were recorded on a Tecnai G2 F30 S-TWIN HR-TEM (FEI, Hillsboro, USA) operating at 200 kV. The samples were drop casted into 400 mesh carbon coated copper grid and it was allowed to dry before imaging. The detection limit or limit of detection (LOD) mentioned in the manuscript, is the lowest quantity/amount of analyte that can be distinguished from the control (sample having no analyte).

3. Results and discussion


In the current work, a new sensing strategy is reported for the first time through a single-step interference synthesis process of using ascorbic acid (AA) as a reducing agent in the

formation of Ag nanoparticles. AA is a green chemical, non-toxic and environment friendly. Hence, it provides a green sensing platform. Interference/interruption of the synthesis of nanoparticles for sensing analytes is one of the least explored fields [30,31]. Single-step sensing process is realized with the interference synthesis of Ag nanoparticles using AA as the reducing agent which has a specific selectivity towards its interaction with the adulterant melamine in raw milk. Although there are many proteins and other chemicals present, AA does not react with them if the milk pre-processing step is done. To eliminate any further need for bringing in selectivity, an inherent selectivity towards the analyte was introduced based on the choice of reducing agent in the interference synthesis of Ag nanoparticles. Hence, there is no additional requirement of chemical modification to incorporate selectivity in interference sensing when compared to conventional two-step sensing process, wherein functionalizing the already synthesized nanoparticles to the analyte for incorporating the selectivity is imperative. Here, a simple visual inspection enables detection of the presence of melamine by the color change induced.

This proposed sensing mechanism is instantaneous with a limit of detection up to 0.1 parts per million (ppm). The allowed limit for melamine levels in milk varies country wise. The increase in concentration of melamine interferes with the synthesis and subsequent spectral change can be monitored by UV-Vis spectroscopy (Figure 1). Also, this sensing strategy gives a colorimetric change which is visible to naked eye.

Previously, the sensing of melamine and other analytes were only reported for already prepared nanoparticles, followed by a chemical modification and aggregation leading to sensing [32–34], whereas, a new sensing scheme in which the synthesis itself is altered leading to the change in size and morphology of the formed nanoparticles is being reported here. In the

conventional two-step sensing process, size and morphology of the nanoparticles are already stabilized but in the proposed single-step sensing, the size and shape gets altered/modified during the interference synthesis process itself. Figure 1 inset shows the colorimetric change of different concentrations of melamine from 0.1 ppm to 1000 ppm. It depicts the color change during the interaction of analytes with the formation of Ag nanoparticles. The Ag nanoparticles showed a sharp surface plasmon resonance (SPR) peak at 398 nm. The change in the SPR can be determined spectrophotometrically. The decrease in absorbance is due to the formation of lower number of nanoparticles.

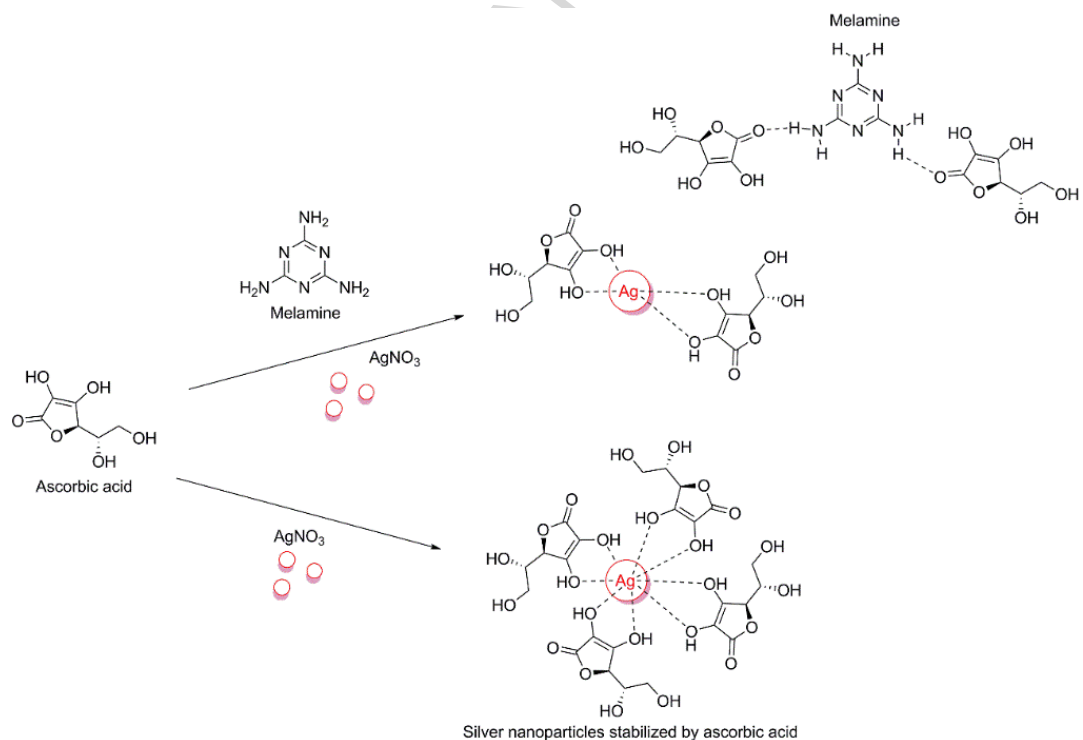

Scheme 1 Schematic illustration of the possible mechanism of interference green synthesis of Ag nanoparticles and hydrogen-bonding interaction between melamine and AA based sensing of melamine.

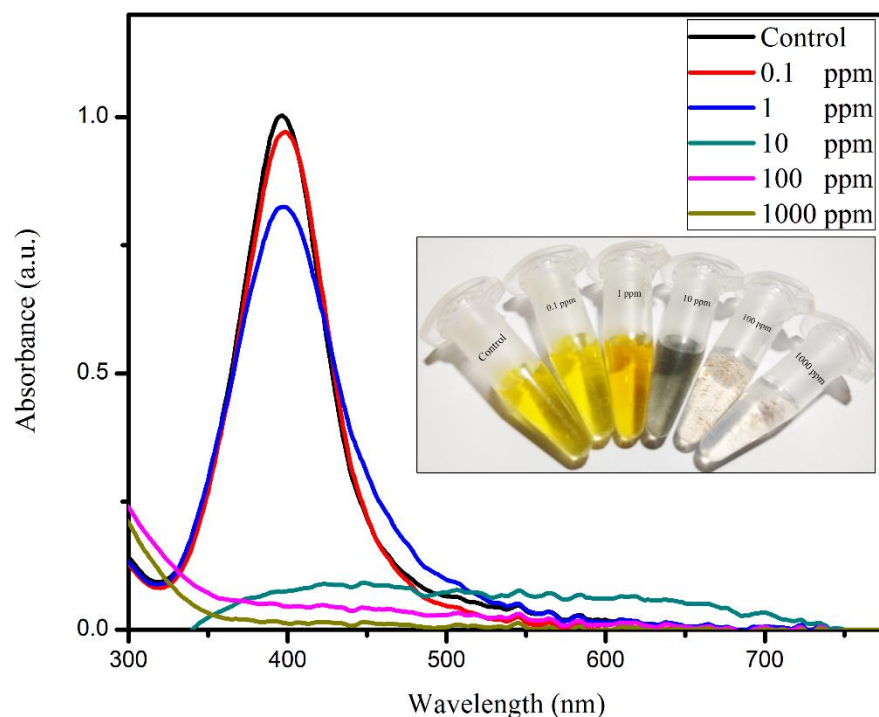


Figure 1 UV-Vis absorption spectra of interference green synthesized Ag. The inset shows the photograph of interference green synthesized Ag nanoparticles with different concentration of melamine (0.1 to 1000 ppm, Control: 0 ppm).

carried out by possible chemicals found in milk that may interfere with the synthesis. The selectivity was done against 100 ppm concentration of lysine, dextrose, glycine, leucine, citric acid, lactose, zinc, sodium, melamine and control (water). Figure 2 shows the bar diagram depicting the selectivity test carried out using other analytes against absorbance at 398 nm. Melamine interfered green synthesis resulted in an observable color change while rest of the analytes did not show much difference from the control (Fig. S1). When melamine is added, the synthesis gets disrupted with an intensity variation in absorbance according to the concentration of melamine.

The interference in the synthesis of Ag nanoparticles may be attributed to the strong hydrogen-bonding interaction between the reducing agent and analyte. The schematic

representation of the deduced mechanism of interference green synthesis based sensing is presented in Scheme 1. Melamine is a strong nucleophile which contains nine hydrogen-bonding sites. Thus, melamine would specifically interact with AA through a hydrogen-bonding interaction to interfere in the synthesis of Ag nanoparticles. The hydrogen-bonding interaction consumes a certain amount of AA thereby not having enough reducing agent to reduce Ag ions, resulting in the weakening of AA's reducing ability, thus resulting in the interruption/interference of Ag nanoparticles formation. The synthesis and sensing happens within seconds, creating a desirable platform for ultra-fast in-situ detection of melamine.

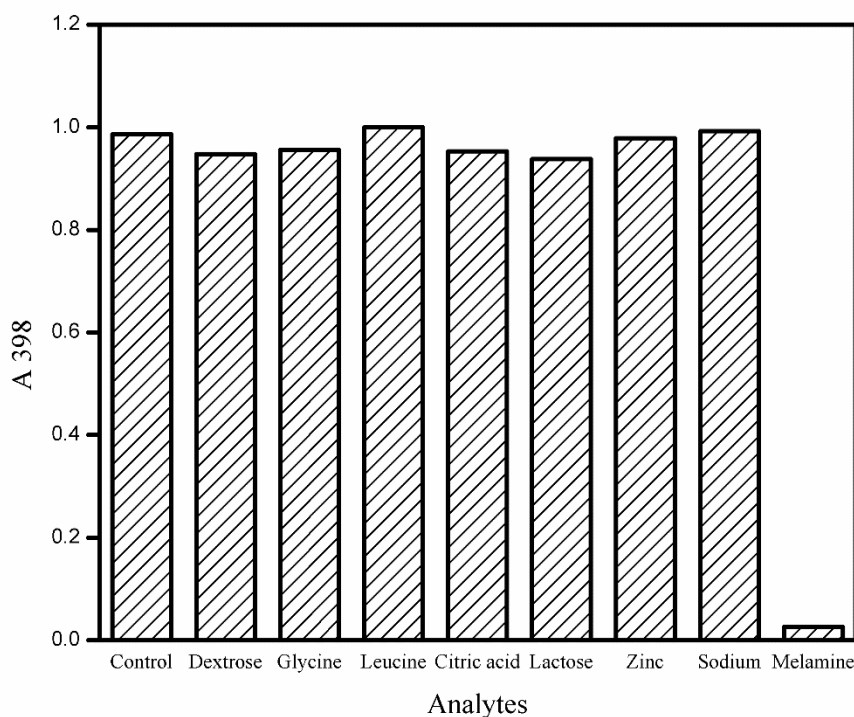


Figure 2 Selectivity test carried with different analytes at 100 ppm concentration against 398 nm wavelength.

The linear correlation coefficient was calculated by taking the absorbance intensity at 398 nm. R^2 value was found to be 0.9908. In the Figure 3A, different melamine concentrations were

plotted against the absorbance at 398 nm wavelength. In order to understand the spectral difference in the range of 0.1 ppm to 10 ppm, the sensing experiments were performed again. The Figure 3B shows the differential spectral change according to the various concentrations of melamine. Hence, it can be used as a good sensor to know the concentration of melamine in accordance with the allowed limit of melamine in different countries.

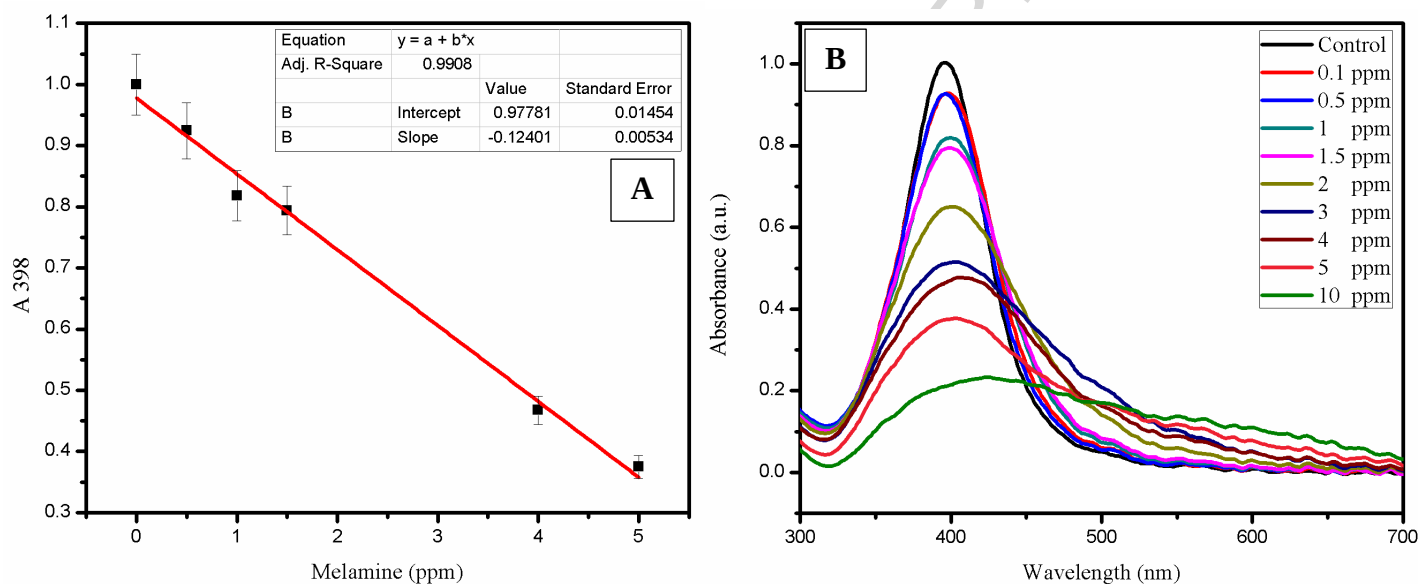


Figure 3 **A)** The calibration curve between absorbance at 398 nm and concentration of melamine for the calculation of linearly dependent coefficient. **B)** UV-Vis absorption spectra of interference green synthesized Ag with different concentration of melamine (0.1 to 10 ppm, Control: 0 ppm).

TEM study was conducted on synthesized Ag nanoparticles with and without melamine to understand the morphological changes. The TEM images (Figure 4) show that there is a significant change in the morphology of the nanoparticles being formed. The presence of analyte leads to the irregular formation of nanoparticles whereas the absence of analytes gives rise to monodispersed particles in the size range of 7-15 nm. The TEM images give a clear indication of analytes inhibiting the formation of nanoparticles.

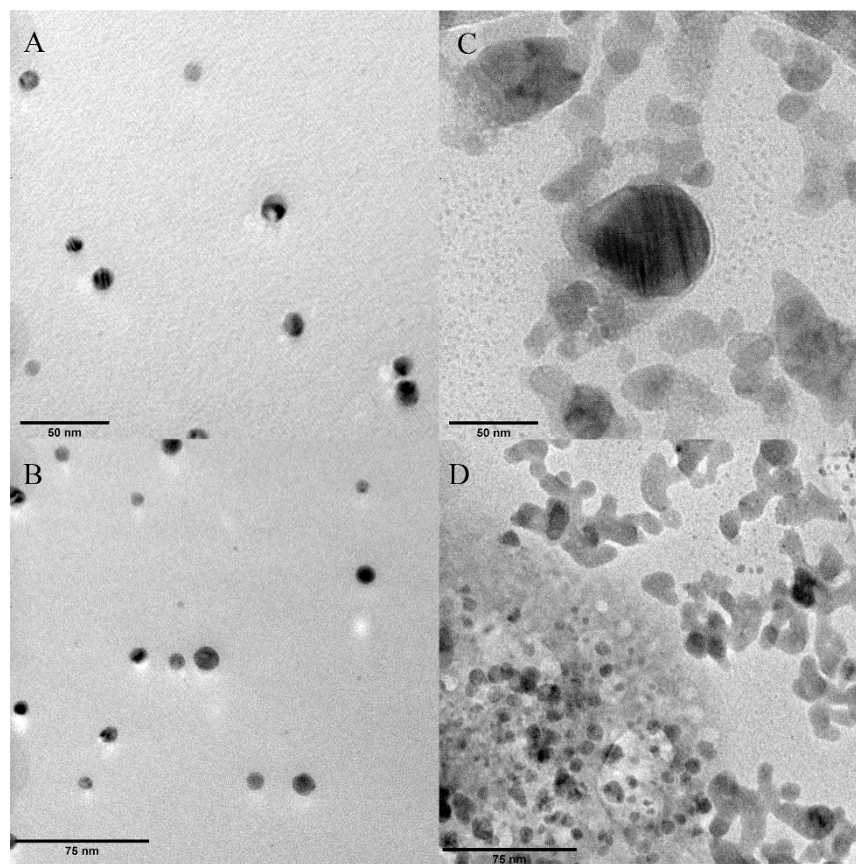


Figure 4 Different scales of TEM images of interference green synthesis of Ag nanoparticles with and without melamine (A, B – Without melamine; C, D – With 100 ppm melamine; Scale: A, C – 50 nm; B, D – 75 nm).

In order to understand the practical applicability of interference green synthesized Ag nanoparticles for real-time milk samples, direct analysis of raw milk was also performed. A pre-processing step was implemented to extract the filtrate, for separating the possible interfering chemicals that may be found in milk. The milk pre-processing step was carried out according to the previous reports with a slight modification [15]. The spiked melamine milk concentrations were divided into two sets. One set was taken for HPLC measurements and the other set for validation using interference green synthesis. The HPLC chromatographs for different concentrations of melamine spiked milk samples is shown in the Figure 5B. The corresponding melamine peak was observed at 3.5 min from the standard melamine chromatogram. With the

increased concentration of melamine, a proportionate increase in the peak corresponding to melamine can be observed. The melamine sensing for the pre-processed milk was carried out using interference green synthesis of Ag nanoparticles, which is depicted in the Figure 5A. The spectral response was very good and the data obtained followed the similar trend with that of HPLC. The color change for the corresponding can be visualized as shown in Fig. S2.

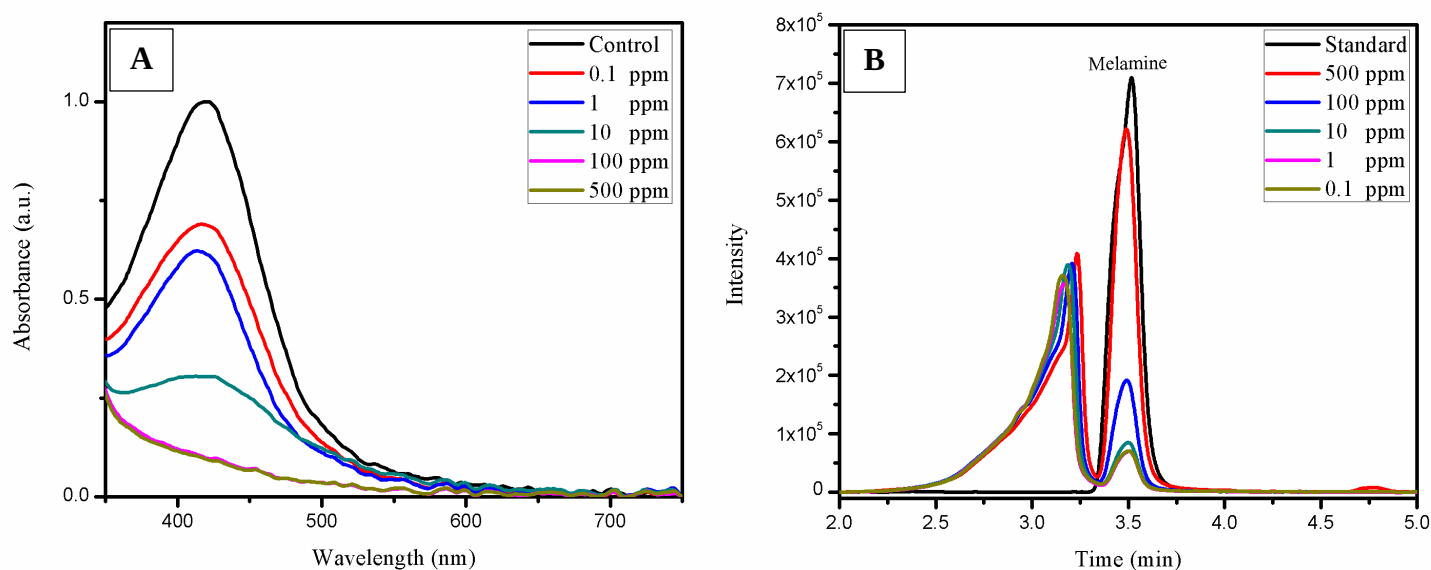


Figure 5 A) UV-Vis absorption spectra of Ag nanoparticles synthesized with different concentrations of melamine (0.1-500 ppm) from pre-processed milk **B)** HPLC chromatograms obtained after spiking milk with different concentrations of melamine; 0.1-500 ppm (Standard: 1000 ppm melamine in water, Column: C18, UV detection: 240 nm, Injection volume: 3 μ L, Mobile phase; Acetonitrile: H₂O - 70:30, Flow rate: 0.7 mL/min).

4. Conclusions

To conclude, a cost effective and simple interference green synthesis of Ag nanoparticles for sensing of milk adulterant (melamine) has been demonstrated. Ag nanoparticle shows sharp

SPR peak at 398 nm, and the differential change was monitored as a function of concentration of melamine. Limit of detection of melamine using this method was found out to be 0.1 ppm which is well below the prescribed limits of India, US, European Union (EU) and China. The formation and morphology of Ag nanoparticles was disrupted significantly due to the interaction of melamine with AA, during the synthesis process itself. The analyte concentration with respect to the formation of nanoparticles was monitored using UV-Vis spectroscopy and validated against HPLC, the gold standard test for melamine. Melamine sensing was achieved in a single-step when compared to conventional two-step synthesis and post-sensing mechanism. This sensing is rapid with a linearly dependent coefficient of 0.9908 and it exhibited excellent selectivity against other possible interfering agents. The present method involves sensing of melamine by simple visualization and avoids the need for sophisticated and expensive instruments. Work is in progress to explore the possibility of detection of melamine from raw milk and other infant formulas; and the realization of a robust microfluidic integrated sensor for real-time field applications.

Acknowledgements

The authors would like to thank Dr. Annaraj B. (Department of Inorganic and Physical Chemistry, IISc Bangalore) for his generous help in the preparation of ChemDraw scheme. The financial support provided by Social Innovation Programme for Products: Affordable and Relevant to Societal Health (SPARSH) project by Biotechnology Industry Research Assistance Council (BIRAC) is greatly appreciated. Varun S. would like to express his deep gratitude to all faculty members of Amity Institute of Nanotechnology, Amity University (Noida) for their support and permission to carry out his master thesis project in IISc.


References

- [1] G. Huang, W. Xu, M. a Visbal-Onufrak, Z. Ouyang, R.G. Cooks, Direct analysis of melamine in complex matrices using a handheld mass spectrometer., *Analyst*. 135 (2010) 705–711. doi:10.1039/b923427f.
- [2] Q. Zhou, N. Liu, Z. Qie, Y. Wang, B. Ning, Z. Gao, Development of gold nanoparticle-based rapid detection kit for melamine in milk products, *J. Agric. Food Chem.* 59 (2011) 12006–12011. doi:10.1021/jf202919a.
- [3] L.C. Mecker, K.M. Tyner, J.F. Kauffman, S. Arzhantsev, D.J. Mans, C.M. Gryniewicz-Ruzicka, Selective melamine detection in multiple sample matrices with a portable Raman instrument using surface enhanced Raman spectroscopy-active gold nanoparticles, *Anal. Chim. Acta*. 733 (2012) 48–55. doi:10.1016/j.aca.2012.05.001.
- [4] T.H. Tsai, S. Thiagarajan, S.M. Chen, Detection of melamine in milk powder and human urine, *J. Agric. Food Chem.* 58 (2010) 4537–4544. doi:10.1021/jf904554s.
- [5] R.L. Melnick, G.A. Boorman, J.K. Haseman, R.J. Montali, J. Huff, Urolithiasis and bladder carcinogenicity of melamine in rodents, *Toxicol. Appl. Pharmacol.* 72 (1984) 292–303. doi:10.1016/0041-008X(84)90314-4.
- [6] C.A. Brown, K. Jeong, R.H. Poppenga, B. Puschner, D.M. Miller, A.E. Ellis, K. Kang, S. Sum, A.M. Cistola, S.A. Brown, Outbreaks of renal failure associated with melamine and cyanuric acid in dogs and cats in 2004 and 2007, *J. Vet. Diagnostic Investig.* 19 (2007) 525–531.
- [7] B. Puschner, R.H. Poppenga, L.J. Lowenstine, M.S. Filigenzi, P.A. Pesavento, Assessment of melamine and cyanuric acid toxicity in cats, *J. Vet. Diagnostic Investig.* 19 (2007) 616–624. doi:10.1177/104063870701900602.
- [8] H. Xin, R. Stone, Tainted milk scandal. Chinese probe unmasks high-tech adulteration with melamine., *Science*. 322 (2008) 1310–1. doi:10.1126/science.322.5906.1310.
- [9] J. Li, H.Y. Qi, Y.P. Shi, Determination of melamine residues in milk products by zirconia hollow fiber sorptive microextraction and gas chromatography-mass spectrometry, *J. Chromatogr. A*. 1216 (2009) 5467–5471. doi:10.1016/j.chroma.2009.05.047.
- [10] D. He, X. Zhang, B. Gao, L. Wang, Q. Zhao, H. Chen, H. Wang, C. Zhao, Preparation of magnetic molecularly imprinted polymer for the extraction of melamine from milk followed by liquid chromatography-tandem mass spectrometry, *Food Control*. 36 (2014) 36–41. doi:10.1016/j.foodcont.2013.07.044.
- [11] Y. Qi, G. Li, C. Wei, L. Zhao, Preparation of Magnetic Molecularly Imprinted Polymer for Melamine and its Application in Milk Sample Analysis by HPLC Abstract Materials, *J. Biomed. Sci.* 5 (2016) 1–10. doi:http://dx.doi.org/10.4172/2254-609X.100030 Journal.
- [12] M.L. Yola, T. Eren, N. Atar, S. Wang, Adsorptive and photocatalytic removal of reactive dyes by silver nanoparticle-colemanite ore waste, *Chem. Eng. J.* 242 (2014) 333–340. doi:10.1016/j.cej.2013.12.086.
- [13] N. Atar, T. Eren, B. Demirdögen, M.L. Yola, M.O. Çağlayan, Silver , gold , and silver @

- gold nanoparticle-anchored L -cysteine-functionalized reduced graphene oxide as electrocatalyst for methanol oxidation, *Ionics* (Kiel). 21 (2015) 2285–2293. doi:10.1007/s11581-015-1395-1.
- [14] M.L. Yola, T. Eren, N. Atar, H. Saral, I. Ermis, Direct-methanol Fuel Cell Based on Functionalized Graphene Oxide with Mono-metallic and Bi-metallic Nanoparticles : Electrochemical Performances of Nanomaterials for Methanol Oxidation, *Electroanalysis*. 28 (2016) 570–579. doi:10.1002/elan.201500381.
- [15] N. Atar, T. Eren, M.L. Yola, H. Gerengi, S. Wang, Fe @ Ag nanoparticles decorated reduced graphene oxide as ultrahigh capacity anode material for lithium-ion battery, *Ionics*. 21 (2015) 3185–3192. doi:10.1007/s11581-015-1520-1.
- [16] T. Eren, N. Atar, M.L. Yola, H. Karimi-maleh, A.T. Çolak, A. Olgun, Facile and green fabrication of silver nanoparticles on a polyoxometalate for Li-ion battery, *Ionics* (Kiel). 21 (2015) 2193–2199. doi:10.1007/s11581-015-1409-z.
- [17] M. Lütfi, V. Kumar, T. Eren, A.E. S, N. Atar, A novel electro analytical nanosensor based on graphene oxide / silver nanoparticles for simultaneous determination of quercetin and morin, 120 (2014) 204–211. doi:10.1016/j.electacta.2013.12.086.
- [18] M. Lüt, V. Kumar, N. Atar, New molecular imprinted voltammetric sensor for determination of ochratoxin A, 61 (2016) 368–375. doi:10.1016/j.msec.2015.12.057.
- [19] Y. Ma, H. Niu, X. Zhang, Y. Cai, One-step synthesis of silver/dopamine nanoparticles and visual detection of melamine in raw milk, *Analyst*. 136 (2011) 4192. doi:10.1039/c1an15327g.
- [20] J. Song, F. Wu, Y. Wan, L. Ma, Colorimetric detection of melamine in pretreated milk using silver nanoparticles functionalized with sulfanilic acid, *Food Control*. 50 (2015) 356–361. doi:10.1016/j.foodcont.2014.08.049.
- [21] H. Ping, M. Zhang, H. Li, S. Li, Q. Chen, C. Sun, T. Zhang, Visual detection of melamine in raw milk by label-free silver nanoparticles, *Food Control*. 23 (2012) 191–197. doi:10.1016/j.foodcont.2011.07.009.
- [22] P. Kaleeswaran, T. Nandhini, K. Pitchumani, Naked eye sensing of melamine : aggregation induced recognition by sodium D -gluconate, *New J. Chem*. 40 (2016) 3869–3874. doi:10.1039/C5NJ03083H.
- [23] K. Ai, Y. Liu, L. Lu, Hydrogen-Bonding Recognition-Induced Color Change of Gold Nanoparticles for Visual Detection of Melamine in Raw Milk and Infant Formula - *Journal of the American Chemical Society* (ACS Publications), (2009) 9496–9497. doi:10.1021/ja9037017.
- [24] F. Wei, R. Lam, S. Cheng, S. Lu, D. Ho, N. Li, Rapid detection of melamine in whole milk mediated by unmodified gold nanoparticles, *Appl. Phys. Lett*. 96 (2010) 2008–2011. doi:10.1063/1.3373325.
- [25] P. Ni, H. Dai, Y. Wang, Y. Sun, Y. Shi, J. Hu, Z. Li, Visual detection of melamine based

- on the peroxidase-like activity enhancement of bare gold nanoparticles, *Biosens. Bioelectron.* 60 (2014) 286–291. doi:10.1016/j.bios.2014.04.029.
- [26] Xiaosheng Liang, H. Wei, Z. Cui, J. Deng, Z. Zhang, X. Youab, X.-E. Zhang, Colorimetric detection of melamine in complex matrices based on cysteamine-modified gold nanoparticles, *Analyst.* 136 (2011) 179–783. doi:10.1016/j.foodchem.2014.11.098.
- [27] T. Eren, N. Atar, A Molecular Imprinted Voltammetric Sensor Based on Carbon Nitride Nanotubes : Application to Determination of Melamine, 163 (2016) 588–593. doi:10.1149/2.0311613jes.
- [28] K. Daniel, Microbicidal Tissue Paper Using Green Synthesized Silver Nanoparticles, *Curr. Nanosci.* 11(1) (2015) 64–68. doi:10.2174/1573413710666140909211129.
- [29] R. Yang, W. Huang, L. Zhang, M. Thomas, X. Pei, Milk adulteration with melamine in China : crisis and response, *Qual. Assur. Saf. Crop. Foods.* 1.2 (2009) 111–116. doi:10.1111/j.1757-837X.2009.00018.x.
- [30] H. Wang, D. Chen, L. Yu, M. Chang, L. Ci, One-step, room temperature, colorimetric melamine sensing using an in-situ formation of silver nanoparticles through modified Tollens process, *Spectrochim. Acta - Part A Mol. Biomol. Spectrosc.* 137 (2015) 281–285. doi:10.1016/j.saa.2014.08.041.
- [31] X. Zhang, Z. Wu, Y. Xue, Y. Zhang, H. Zhao, Y. He, X. Li, Z. Yuan, Colorimetric detection of melamine based on the interruption of the synthesis of gold nanoparticles, *RSC Anal. Methods.* 5 (2013) 1930–1934.
- [32] S. Zeng, M. Cai, H. Liang, J. Hao, Size-dependent colorimetric visual detection of melamine in milk at 10 ppb level by citrate-stabilized Au nanoparticles, *Anal. Methods.* 4 (2012) 2499. doi:10.1039/c2ay25319d.
- [33] N. Vasimalai, S. Abraham John, Picomolar melamine enhanced the fluorescence of gold nanoparticles: Spectrofluorimetric determination of melamine in milk and infant formulas using functionalized triazole capped gold nanoparticles, *Biosens. Bioelectron.* 42 (2013) 267–272. doi:10.1016/j.bios.2012.10.023.
- [34] H. Dai, Y. Shi, Y. Wang, Y. Sun, J. Hu, P. Ni, Z. Li, A carbon dot based biosensor for melamine detection by fluorescence resonance energy transfer, *Sensors Actuators, B Chem.* 202 (2014) 201–208. doi:10.1016/j.snb.2014.05.058.

Graphical abstract

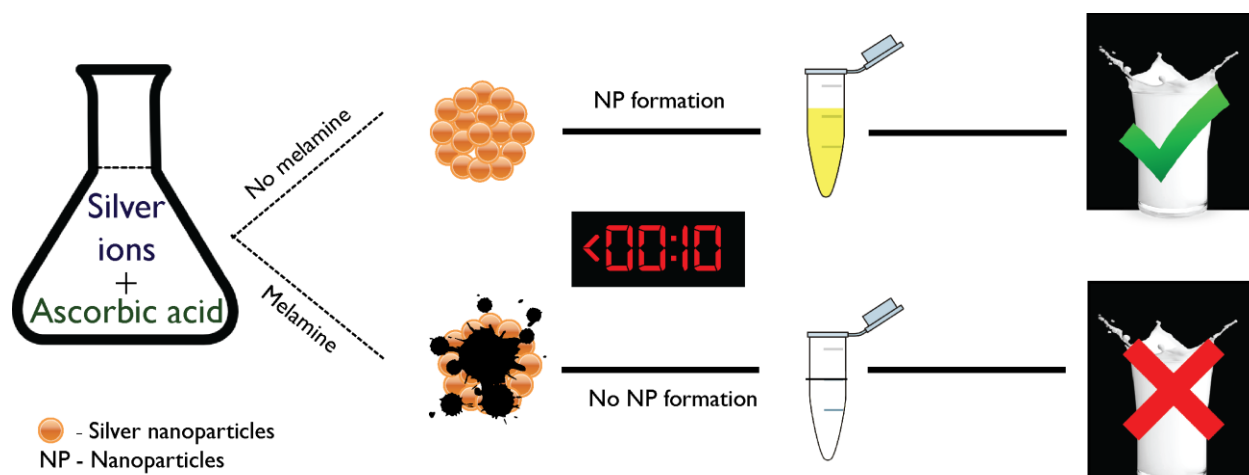

Highlights

- Rapid detection of milk adulterant melamine based on interference green synthesis.
- Green chemical ascorbic acid used as the reducing agent for interference sensing.
- Enabling in-situ sensing of melamine from milk with a limit of detection of 0.1 ppm.
- Presence of analyte inhibits the nanoparticle formation.