

Review

How Do Enzymes ‘Meet’
Nanoparticles and
Nanomaterials?Ming Chen,^{1,2,*} Guangming Zeng,^{1,2,*} Piao Xu,^{1,2} Cui Lai,^{1,2}
and Lin Tang^{1,2}

Enzymes are fundamental biological catalysts responsible for biological regulation and metabolism. The opportunity for enzymes to ‘meet’ nanoparticles and nanomaterials is rapidly increasing due to growing demands for applications in nanomaterial design, environmental monitoring, biochemical engineering, and biomedicine. Therefore, understanding the nature of nanomaterial–enzyme interactions is becoming important. Since 2014, enzymes have been used to modify, degrade, or make nanoparticles/nanomaterials, while numerous nanoparticles/nanomaterials have been used as materials for enzymatic immobilization and biosensors and as enzyme mimicry. Among the various nanoparticles and nanomaterials, metal nanoparticles and carbon nanomaterials have received extensive attention due to their fascinating properties. This review provides an overview about how enzymes meet nanoparticles and nanomaterials.

Focusing on the Interaction of Enzymes with Nanoparticles and Nanomaterials

The rapid development of nanotechnology has significantly increased the opportunity for enzymes to interact with nanoparticles and nanomaterials. Demands to bring nanoparticles, nanomaterials, and enzymes together for applications in biomedicine, biochemical engineering, environmental monitoring, nanoparticle design, and biosensor continue to increase. There has been considerable progress in the field of interactions between enzymes and nanoparticles/nanomaterials since 2014, across a wide variety of interactions such as enzymatic modification or degradation of nanoparticles/nanomaterials, and enzymatic immobilization and biosensors with nanoparticles/nanomaterials. During this period, nanoparticles and nanomaterials have been applied to adjust enzyme activity and to affect enzymatic structures and functions. Simultaneously, reports emerged of enzymes that are capable of modifying nanoparticle/nanomaterial properties to develop their assemblies or conjugates. Enzymatic immobilization on nanoparticles or nanomaterials based on rational design and optimization can significantly enhance enzymatic catalytic performance. Incorporation of nanoparticles or nanomaterials generally increases the stability and sensitivity of enzyme-based biosensors, because the nanoparticles or nanomaterials impart their unique intrinsic properties to the biosensors. In addition to these applications of enzyme/nanomaterial interfaces, the potential environmental risks of nanoparticles or nanomaterials have elicited research interest in the enzymatic degradation of nanoparticles and nanomaterials [1,2]. Natural enzymes present inherent drawbacks such as easy inactivation and time-consuming extraction [3], so enzyme nanoparticles and enzyme mimics of nanoparticles have been fabricated to overcome these drawbacks. While a number of previous reviews have focused on the protein–nanoparticle interface and

Trends

There have been several pathways for the contact between nanoparticles, nanomaterials, and enzymes: (i) enzymatic modification of nanoparticles and nanomaterials; (ii) enzymatic immobilization and biosensor development by nanoparticles or nanomaterials; (iii) enzymatic degradation of nanoparticles and nanomaterials; (iv) enzyme nanoparticles; and (v) enzyme mimics of nanoparticles or nanomaterials.

Unique physiochemical properties of nanoparticles and nanomaterials help enhance the performance of enzymes and biosensors.

Inherent drawbacks of native enzymes can be overcome, by processing enzymes into nanoparticles or by using nanozymes instead.

¹College of Environmental Science and Engineering, Hunan University, Changsha 410082, China

²Key Laboratory of Environmental Biology and Pollution Control (Hunan University), Ministry of Education, Changsha 410082, China

*Correspondence:
mchensn@hnu.edu.cn (M. Chen) and
zgming@hnu.edu.cn (G. Zeng).

interactions, they did not emphasize enzymes and instead treated them as common proteins [4–7]. However, enzymes are different from common proteins, because they are catalysts in living organisms that play very important roles in biological regulation and metabolism. Thus, in this Review we provide an insight into the interactions between enzymes and nanoparticles/nanomaterials and associated variations in enzymes, including which enzymes ‘meet’ nanoparticles and nanomaterials; which nanoparticles and nanomaterials meet enzymes; and the main pathways through which enzymes meet nanoparticles and nanomaterials. This review discusses important issues related to the interactions of nanoparticles and nanomaterials with enzymes, with special emphasis on papers published in the past 3 years. Over >3 years, >25 nanoparticles/nanomaterials have met >40 enzymes. Information on each of these enzymes was adapted from the well-known BRENDA enzyme database [8] (<http://www.brenda-enzymes.org/>), and corresponding links are provided in Table 1. Some of these enzymes overlap according to enzymatic definition in Table 1, such as peroxidase, myeloperoxidase, and eosinophil peroxidase, where myeloperoxidase and eosinophil peroxidase belong to the peroxidases. However, in this Review, they are considered different to give a faithful account of what enzymes are in contact with nanoparticles or nanomaterials. For organisms that contain these enzymes, only one or two examples are provided for each enzyme.

Interactions of Enzymes with Nanoparticles or Nanomaterials and Associated Property Changes

Nanoparticles or nanomaterials have been increasingly used for a variety of applications [9–13]. Many of these applications require the participation of enzymes, which results in favorable or unfavorable changes in physicochemical properties of enzymes or nanoparticles/nanomaterials. For example, the presence of enzymes may impair the intrinsic physical properties of single-walled carbon nanotubes (SWCNTs) by nonspecific adsorption onto SWCNTs [14]. Proteins or enzymes can bind to the surface of nanoparticles to form the nanoparticle–protein corona, which provides a biological identity to the nanoparticles [7,15–17]. It is critical to find out how structural and functional changes in enzymes are caused by nanoparticles and nanomaterials. In general, enzymatic adsorption onto nanoparticles and nanomaterials will cause conformational transitions, accompanied by the inhibition or enhancement of enzyme activity. A range of nanoparticles and nanomaterials including CNTs, graphene, fullerene derivatives (Table 2), and metal nanoparticles (Table 3), has been demonstrated to have different effects on enzymatic structures or activities. The differing effects depend on the types and orientations of enzymes, physical properties of nanomaterials (e.g. shape and size), chemical groups attached to nanomaterials, and environmental conditions [18–21]. Different enzymes have inconsistent amino acid composition and 3D structures, which lead to different interactions with nanoparticles and nanomaterials. Enzyme orientations towards nanoparticles and nanomaterials are critical, because improper orientations could make the enzymatic active sites blocked or hindered by nanoparticles/nanomaterials or other adjacent molecules [19]. The physicochemical properties of nanoparticles and nanomaterials, together with the surrounding environmental conditions (e.g. pH and temperature), affect their binding orientations and interactions with enzymes, stability of enzymes, or substrate accessibility.

The effects of nanoparticles and nanomaterials on the structures and activity of several enzymes have been investigated, including lysozyme, α -chymotrypsin, protein tyrosine phosphatase 1B, laccase, haloalkane dehalogenase, lignin peroxidase, naphthalene 1,2-dioxygenase, manganese peroxidase, horseradish peroxidase, NADPH oxidase, and β -galactosidase. The first enzyme we review here is lysozyme, which has been extensively applied as a model enzyme to explore the interactions between nanoparticles/nanomaterials and enzymes. It is reported that adsorption of lysozymes onto SWCNTs is inhibited by arginine, because arginine inhibits the interactions of SWCNTs with its amino acid residues [14]. Du *et al.* [22] investigated the adsorption of lysozyme onto three functionalized

Table 1. Information on Enzymes Interacting with Nanoparticles or Nanomaterials

Enzyme	Description	Organisms
Lysozyme ⁱ	Model protein to investigate the interactions between protein and nanoparticles	<i>Brassica oleracea</i> , <i>Rattus norvegicus</i>
Laccase ⁱⁱ	Ligninolytic enzyme; can oxidize lignin, and various organic pollutants such as polycyclic aromatic hydrocarbons (PAHs).	<i>Trametes versicolor</i> , <i>Rhizoctonia solani</i>
Haloalkane dehalogenase ⁱⁱⁱ	Can degrade β -hexachlorocyclohexane and other compounds.	<i>Aeromicrobium marinum</i> , <i>Mycobacterium smegmatis</i>
Lignin peroxidase ^{iv}	Ligninolytic enzyme.	<i>Phanerochaete chrysosporium</i> , <i>Trametesopsis cervina</i>
Naphthalene 1,2-dioxygenase ^v	Participating in the degrading pathways of some PAHs such as anthracene and naphthalene.	<i>Escherichia coli</i> , <i>Pseudomonas putida</i>
Manganese peroxidase ^{vi}	Catalyzing the reaction: $2 \text{ Mn(II)} + 2 \text{ H}^+ + \text{H}_2\text{O}_2 = 2 \text{ Mn(III)} + 2 \text{ H}_2\text{O}$.	<i>Phanerochaete chrysosporium</i> , <i>Trametes hirsuta</i>
α -Chymotrypsin ^{vii}	Carrying out the hydrolysis of protein and polypeptides.	<i>Homo sapiens</i> , <i>Spodoptera frugiperda</i>
Protein tyrosine phosphatase ^{viii}	Catalyzing the reaction: [protein]-tyrosine phosphate + H_2O = [protein]-tyrosine + phosphate.	<i>Drosophila melanogaster</i> , <i>Gallus gallus</i>
Feruloyl esterase ^{ix}	Catalyzing the hydrolysis of ester bonds in plant cell walls into ferulic acid, and has been applied in medicine, paper-pulp and food industries.	<i>Anaeromyces mucronatus</i> , <i>Aspergillus niger</i>
Aminoacylase ^x	Also known as N-acyl-L-amino-acid aminohydrolase, catalyzing several reaction types, such as the hydrolysis of amide bond and N-acetylated amino acids.	<i>Alcaligenes faecalis</i> , <i>Bos taurus</i> ,
Bovine serum amine oxidase	Copper-containing enzyme composed of a homodimer, being involved in the oxidative deamination of primary amines.	<i>B. taurus</i>
Plant esterase	Can be found in numerous plants and is highly sensitive to organophosphates (EC 3.1.1.X).	<i>Oryza sativa</i> , <i>Triticum aestivum</i>
β -Galactosidase ^{xi}	Can convert lactose into glucose and galactose.	<i>Aspergillus aculeatus</i> , <i>Bacillus circulans</i>
Acetylxylo-esterase ^{xii}	Catalyzing the deacetylation of xylans and xylo-oligosaccharides.	<i>Aspergillus ficuum</i> , <i>Bacillus pumilus</i> ,
Glucose oxidase ^{xiii}	Catalyzing the reaction: β -D-glucose + O_2 = D-glucono-1,5-lactone + H_2O_2 .	<i>Aspergillus</i> sp. <i>Penicillium canescens</i>
Cytochrome <i>bd</i> oxidase ^{xiv}	Also known as menaquinol oxidase (H ⁺ -transporting); catalyzing the reaction: $2 \text{ menaquinol} + \text{O}_2 = 2 \text{ menaquinone} + 2 \text{ H}_2\text{O}$.	<i>Bacillus subtilis</i> , <i>E. coli</i>
Sulfite oxidase ^{xv}	Catalyzing the reaction: sulfite + O_2 + H_2O = sulfate + H_2O_2 .	<i>H. sapiens</i> , <i>B. taurus</i>
Peroxidase ^{xvi}	Catalyzing the reaction: $2 \text{ phenolic donor} + \text{H}_2\text{O}_2 = 2 \text{ phenoxyl radical of the donor} + 2 \text{ H}_2\text{O}$.	<i>A. sativum</i> , <i>H. sapiens</i>
Lactoperoxidase	Heme-containing peroxidase.	<i>H. sapiens</i> , <i>M. musculus</i>
Myeloperoxidase ^{xvii}	Catalyzing the reaction: $\text{Cl}^- + \text{H}_2\text{O}_2 + \text{H}^+ = \text{HClO} + \text{H}_2\text{O}$.	<i>B. taurus</i> , <i>H. sapiens</i>
Eosinophil peroxidase	Heme peroxidase; catalyzing the oxidation of halides.	<i>H. sapiens</i> , <i>M. musculus</i>
Glucose dehydrogenase	Found in <i>Ewingella americana</i> ; composed of α , β , γ subunits	<i>Ewingella americana</i>

Table 1. (continued)

Enzyme	Description	Organisms
Microbial esterase	Presented in various microbes.	<i>Enterococcus faecalis</i> V583, <i>Sinorhizobium meliloti</i>
Nitrate reductase ^{xxviii}	Catalyzing conversion of nitrite to nitrate.	<i>Rhodotorula glutinis</i> , <i>Candida nitratophila</i>
DNA methyltransferase ^{xxix}	Enzyme family that is involved in DNA methylation.	<i>H. sapiens</i> , <i>Spiroplasma monobiae</i>
Protein disulfide-isomerase ^{xxx}	Responsible for rearrangement of –S-S– bonds in proteins.	<i>H. sapiens</i> , <i>Oryctolagus cuniculus</i>
DNA ligase	Four DNA ligases are presented in BRENDA: DNA ligase (ATP) (EC 6.5.1.1), DNA ligase (NAD+) (EC 6.5.1.2), DNA ligase (ATP or NAD+) (EC 6.5.1.6) and DNA ligase (ATP, ADP or GTP) (EC 6.5.1.7).	<i>H. sapiens</i> , <i>E. coli</i>
Lipase	Can hydrolyze fats.	<i>Candida rugosa</i>
Glycerol-3-phosphate oxidase ^{xxxi}	Catalyzing the reaction: sn-glycerol 3-phosphate + O ₂ = glycerone phosphate + H ₂ O ₂ .	<i>Mycoplasma pneumoniae</i> , <i>Pediococcus</i> sp.
Glycerol kinase ^{xxxii}	Catalyzing the reaction: ATP + glycerol = ADP + sn-glycerol 3-phosphate.	<i>Candida mycoderma</i> , <i>Elizabethkingia meningoseptica</i>
Cholesterol oxidase ^{xxxiii}	Catalyzing the reaction: cholesterol + O ₂ = cholest-5-en-3-one + H ₂ O ₂ .	<i>Nocardia erythropolis</i> , <i>Schizophyllum commune</i>
Cholesterol esterase ^{xxxiv}	Also called sterol esterase; catalyzing the reaction: sterol ester + H ₂ O = sterol + fatty acid.	<i>Candida rugosa</i> , <i>Rattus</i> sp.
Uricase ^{xxxv}	Also known as urate oxidase or factor-independent urate hydroxylase; catalyzing the reaction: urate + O ₂ + H ₂ O = 5-hydroxyisourate + H ₂ O ₂ .	<i>Arthrobacter pascens</i> , <i>B. taurus</i>
Superoxide dismutase ^{xxxvi}	Catalyzing the reaction: 2 superoxide + 2 H ⁺ = O ₂ ²⁻ + H ₂ O ₂ .	<i>A. sativum</i> , <i>Bacillus</i> sp.
Pullulanase ^{xxxvii}	Catalyzing hydrolysis of O-glycosyl bond.	<i>Enterobacter aerogenes</i> , <i>Fervidobacterium pennivorans</i> ,
Inulinase ^{xxxviii}	Catalyzing endohydrolysis of (2->1)-β-D-fructosidic linkages in inulin.	<i>Aspergillus fumigatus</i> , <i>Bacillus safensis</i>
α-Amylase ^{xxxix}	Catalyzing hydrolysis of α bonds from polysaccharides, such as starch.	<i>Apis mellifera</i> , <i>Bacillus coagulans</i>
Cellulase ^{xxx}	Catalyzing cellulolysis.	<i>Acetivibrio cellulolyticus</i> , <i>Bacillus mycoides</i>
α-Galactosidase ^{xxxxi}	Catalyzing decomposition of glycolipids and glycoproteins whose terminal α-galactosyl moieties are hydrolyzed.	<i>H. sapiens</i> , <i>M. musculus</i>
Diamine oxidase ^{xxxii}	Catalyzing reaction: histamine + H ₂ O + O ₂ = (imidazol-4-yl)acetaldehyde + NH ₃ + H ₂ O ₂ .	<i>B. taurus</i> , <i>Euphorbia characias</i>
Monoamine oxidase ^{xxxiii}	Catalyzing reaction: RCH ₂ NHR' + H ₂ O + O ₂ = RCHO + R'NH ₂ + H ₂ O ₂ .	<i>Avena sativa</i> , <i>Macaca fuscata</i>

multi-walled CNTs (MWCNTs) that were graphitized, carboxylated, or hydroxylated. Hydroxylated MWCNTs had the maximum adsorption capacity, followed by carboxylated and graphitized MWCNTs. Pan *et al.* [23] studied the structural basis and adsorption of T4 lysozyme onto silica nanoparticles, and significant activity loss was found. α-Chymotrypsin is another enzyme that is often used to investigate the effect of nanomaterials on enzymatic activity.

Table 2. Interactions of Enzymes with Carbon Nanomaterials

Nanomaterial	Enzyme	Reason for their interactions	Refs
SWCNT	Lysozyme	Investigating lysozyme adsorption onto SWCNTs	[14]
	Laccase	Exploring the impacts of SWCNT on enzyme-catalyzed oxidation processes	[26]
	Haloalkane dehalogenase	Exploring the impacts of SWCNT on enzyme-catalyzed oxidation processes	[26]
	Lignin peroxidase	Exploring the impacts of SWCNT on enzyme-catalyzed oxidation processes	[26]
	Naphthalene 1,2-dioxygenase	Exploring the impacts of SWCNT on enzyme-catalyzed oxidation processes	[26]
	Manganese peroxidase	Exploring the impacts of SWCNT on enzyme-catalyzed oxidation processes	[26]
	α -Chymotrypsin	Investigating α -chymotrypsin inhibition by SWCNTs	[24]
	Horseradish peroxidase	Biodegradation of SWCNTs	[30]
	Lactoperoxidase	Biodegradation of SWCNTs	[31]
	Myeloperoxidase	Biodegradation of SWCNTs	[32]
MWCNT	Eosinophil peroxidase	Biodegradation of SWCNTs	[33]
	Lysozyme	Investigating lysozyme adsorption onto MWCNTs	[22]
	Human monoamine oxidase B	Establishing a monoamine-sensitive electrochemical biosensor	[34]
	Horseradish peroxidase	Biodegradation of MWCNT	[30]
	Laccase	Enzymatic immobilization	[35]
Fullerene	Cellulase	Enzymatic immobilization	[36]
	Protein tyrosine phosphatase 1B	Analyzing the inhibitory mechanism of protein tyrosine phosphatase 1B towards fullerene derivatives.	[25]
Graphene	Diamine oxidase	A histamine biosensor	[37]
	Plant esterase	Biosensor for detection of methyl parathion and malathion	[38]
	Horseradish peroxidase	Investigating the impacts of graphene-based nanomaterials on the activity or stability of horseradish peroxidase	[27]
	α -Galactosidase	Enzymatic immobilization	[39]
Graphene oxide	Horseradish peroxidase	Investigating the impacts of graphene-based nanomaterials on the activity or stability of horseradish peroxidase	[27]
	Lipase	Enzymatic immobilization	[40]
Reduced graphene oxide	Glucose oxidase	Enzymatic immobilization and biosensing of glucose	[41]
	Horseradish peroxidase	Investigating the impacts of graphene-based nanomaterials on the activity or stability of horseradish peroxidase	[27]

α -Chymotrypsin activity can be regulated by carboxylated SWCNTs. Zhao and Zhou [24] found that the adsorption of α -chymotrypsin onto CNTs leads to changes in the secondary structure of α -chymotrypsin. The authors further pointed out that the binding of α -chymotrypsin to carboxylated CNTs can inhibit enzymatic activity through a competitive-like mode, while the interaction between α -chymotrypsin and pristine CNTs is noncompetitive.

Table 3. Enzymes 'Meet' Inorganic Nanoparticles

Nanoparticle/ nanomaterial	Enzyme	Reason for their interaction	Refs
Fe ₃ O ₄	Aminoacylase	Enzymatic immobilization	[44]
	Glucose oxidase	Enzymatic immobilization	[43]
	Feruloyl esterases	Enzymatic immobilization	[42]
	Acetyl xylan esterase	Enzymatic immobilization	[45]
	DNA ligase	Biosensor for detection of genomic DNA	[56]
	Peroxidase	Enzyme mimic	[57,58]
Au	Bovine serum amine oxidase	Development of a bioconjugation	[46]
	Cytochrome <i>bd</i> oxidase	Detecting the inhibitors of cytochrome <i>bd</i> oxidases	[47]
	Glucose oxidase	Glucose biosensor	[59–61]
	Glucose dehydrogenase	Developing a high current and mediatorless bioanode with low redox potential	[62]
	Glutathione-S transferase	Developing glutathione-S transferase immunosensor	[63]
	Horseradish peroxidase	Developing glutathione-S transferase immunosensor	[63]
	DNA methyltransferase	Electrochemiluminescence biosensor for detection of DNA methyltransferase activity	[64]
	Protein disulfide isomerase	Examination of the hydrodynamic dimension of protein disulfide isomerase	[65]
	DNA ligase	Biosensor for detection of genomic DNA	[56]
	Plant esterase	Biosensor for detection of methyl parathion and malathion	[38]
	DNA methyltransferase	Detection of DNA methyltransferase	[66]
	Peroxidase	Detection of influenza virus	[67]
	Horseradish peroxidase	Biosensors for cyanide measurements	[68]
Ag	Glucose oxidase	Enzymatic immobilization and biosensing of glucose	[41]
	Nitrate reductase	Determination of soil nitrates	[69]
AgX (X is Cl, I or Br)	Peroxidase	Enzyme mimic	[70]
SiO ₂	Laccase	Constructing electroactive nanobiomolecular multilayered architectures	[49]
	Lysozyme	Investigating lysozyme adsorption onto silica nanoparticles	[23]
	Pullulanase	Enzymatic immobilization	[48]
	Inulinase	Enzymatic immobilization	[50]
CdS	Sulfite oxidase	Assembling human sulfite oxidase ITO electrode modified with polyethylenimine-entrapped CdS nanoparticles	[53]
	DNA methyltransferase	Electrochemiluminescence biosensor for detection of DNA methyltransferase activity	[64]
Pt	Peroxidase	Detection of nucleic acids	[71]
	Diamine oxidase	Biosensors for histamine detection	[37]
Cobalt oxide	Microbial esterases	Enzymatic immobilization	[52]

Table 3. (continued)

Nanoparticle/ nanomaterial	Enzyme	Reason for their interaction	Refs
Porous nanorods of ceria	Peroxidase	Enzyme mimic	[72]
CuS	DNA methyltransferase	Detection of DNA methyltransferase	[66]
Cu ²⁺ -g-C ₃ N ₄	Horseradish peroxidase	Enzyme mimic	[73]
Gly-Cu(OH) ₂	Superoxide dismutase	Enzyme mimic	[74]
TiO ₂	NADPH oxidase	Studying the impacts of TiO ₂ nanoparticles on NADPH oxidase	[28]
ZnO	α -amylase	Enzymatic immobilization	[51]

In addition to lysozyme and α -chymotrypsin, other enzymes have also contacted nanoparticles or nanomaterials. One study reported that protein tyrosine phosphatase 1B could be inhibited by fullerene derivatives [25]. Chen *et al.* found that SWCNTs lead to significant conformational changes in C termini of several microbial enzymes including laccase, haloalkane dehalogenase, lignin peroxidase, naphthalene 1,2-dioxygenase, and manganese peroxidase during their applications for oxidation of organic pollutants or lignin model compounds, and some N termini of the enzymes have significant conformational dynamics [26]. Interestingly, different graphene-based nanomaterials [graphene, graphene oxide (GO), and reduced GO (RGO)] exert different effects on the activity or stability of horseradish peroxidase (HRP) [27]. Graphene and GO decrease the enzymatic stability, while RGO enhances the enzymatic stability. All of these graphene-based nanomaterials induce change in secondary structure of HRP.

The effect of TiO₂ on NADPH oxidase has been investigated as well. TiO₂ cannot activate this enzyme without the classical activator, arachidonic acid. However, in the presence of arachidonic acid, TiO₂ nanoparticles increased NADPH oxidase production of superoxide anion by 140% [28]. The interaction between copper oxide nanoparticles and β -galactosidase was investigated, showing that the conformation and activity of β -galactosidase was disrupted by copper oxide nanoparticles [29].

In short, the interaction patterns of enzymes with nanoparticles and nanomaterials and associated property change have been investigated. The properties (e.g. shape, size, and surface chemistry) of nanoparticles and nanomaterials can improve enzymatic performance if rational design is performed, which have attracted researchers' interest in the utilization of nanoparticles and nanomaterials as supports for enzymatic immobilization.

Enzymatic Immobilization on Nanoparticles or Nanomaterials to Improve Enzymatic Performance

Enzyme-mediated reactions often require suitable environmental conditions. Free enzymes are easily inactivated in practical applications [30]. In addition, reusing them is difficult [31]. Enzymatic immobilization on nanoparticles or nanomaterials is expected to solve these problems. However, simple immobilization of enzymes may not achieve the desired enhancement of enzymatic activity, as it may lead to deformation of enzymatic structures and loss of activity. Thus, the optimal immobilization conditions need to be explored.

Over the past few years, there has been significant interest in magnetic nanoparticles as supports for enzymatic immobilization because they allow the enzymes to be easily collected for recycling by a magnet device. Magnetic Fe₃O₄ nanoparticles have been adopted as support

for aminoacylase. Then, the optimum immobilization conditions for aminoacylase on Fe_3O_4 nanoparticles with 3-(aminopropyl)triethoxysilane was demonstrated [32]. A study from Yang *et al.* [31] presented a nanohybrid composed of glucose oxidase (GOX) on Fe_3O_4 @C-silica. The enzyme–material nanohybrid exhibited good thermal and operational stability, and GOX immobilized on the nanohybrid increased the thermal range of stable enzyme activity and retention of the activity after reuse. He *et al.* [30] used magnetic Fe_3O_4 nanoparticles as immobilization support for feruloyl esterases to improve their thermal and operational stability for application in production of ferulic acid. The immobilized recombinant acetyl xylan esterase (rAXE) on Fe_3O_4 magnetic nanoparticles coated with chitosan showed better performance than free rAXE, specifically retaining stability over broader pH and thermal ranges [33].

Gold nanoparticles, another group of extensively used metal nanoparticles, have attracted interest for enzyme immobilization due to their unique physicochemical properties (Table 3). Venditti *et al.* [34] described the development of a bioconjugation composed of gold nanoparticles, poly(3-dimethylammonium-1-propyne hydrochloride) and bovine serum amine oxidase. The enzymatic activity was up to 40% onto this bioconjugation relative to the native enzyme activity. Fournier *et al.* [35] established a setup for the exploration of catalytic activity and inhibition of *Escherichia coli* cytochromes *bd* oxidase by immobilization on the electrodes modified with gold nanoparticles.

Recent research has also focused on enzymatic immobilization onto nanosilica, nano-ZnO, cobalt oxide nanoparticles, and CdS nanoparticles. A novel pullulanase was first purified from *Fontibacillus* sp. strain DSHK 107, and then was immobilized on nanosilica using a glutaraldehyde spacer arm [36]. Immobilized pullulanase showed better thermal stabilization than the free enzyme (15.6- and 16-folds at 35 °C and 50 °C, respectively). This immobilized pullulanase also exhibited a shift in the maximum working pH with a decrease from 6.0 to 5.0. Electroactive nanobiomolecular multilayered architectures have been constructed by the combination of laccase, cytochrome *c*, and silica nanoparticles, where they were used as biocatalyst, electron-shuttle and artificial matrix, respectively [37]. Compared to free enzyme, octadecyl substituted nanoporous silica also enhanced the thermostability and reusability of inulinase from *Aspergillus niger* [38]. Similarly, immobilized diastase α -amylase on nano-ZnO had better thermal stability than the free enzyme [39]. *Bacillus subtilis*-templated cobalt oxide nanoparticles was used to immobilize the microbial esterases. After 15 reuses, the enzyme-based nanostructure retained ~85% of the initial activity [40]. Human sulfite oxidase was assembled on indium tin oxide (ITO) electrode modified with polyethylenimine-entrapped CdS nanoparticles, which facilitates the binding of human sulfite oxidase to the electrode and electron transfer [41].

MWCNTs act as supports for the immobilization of laccase and cellulase (Table 2). The efficiency of immobilized laccase [42] and cellulase [43] reaches an optimal level by reasonably setting the enzyme concentrations, pH and temperature, and contact time. Lignin peroxidase activity of enzymatic extracts from *Ganoderma lucidum* and *Pleurotus ostreatus* increased 27- and 18-fold upon immobilization on CNTs, respectively, as compared to the free enzyme [44]. Besides CNTs, functionalized graphene and GO were also used as supports for the immobilization of cicer α -galactosidase [45] and lipase from *Rhizopus oryzae* [46], respectively. Both graphene and GO increased the thermal stability of enzymes.

Enzymes immobilized on a number of nanoparticles and nanomaterials have shown significant enhancement in enzymatic performance, which strongly depends on enzyme types, support materials, and immobilized conditions. The optimal immobilized conditions for enzymes can be found by repeatedly testing under numerous conditions with different values of pH, temperature, enzymes concentrations, immobilized time, and nanoparticle concentrations. Optimized immobilized enzymes on nanoparticles/nanomaterials often showed four advantages than the

native enzymes: (i) wider temperature range; (ii) broader working pH; (iii) greater thermostability; and (iv) increased reusability. The high surface-to-volume ratio, and chemical, electrical, and optical properties of nanoparticles or nanomaterials can increase enzyme loading, and affect the diffusion of immobilized enzymes and catalytic activity [47]. In addition to the utilization for enzymatic immobilization, nanoparticle, and nanomaterials are also assembled into biosensors for the detection of various molecules.

Enzyme-Based Biosensors with Nanoparticles or Nanomaterials

Electrochemical biosensors based on enzymes are a class of analytical tools to detect a variety of molecules of interest. Enzyme-based biosensors show new properties such as enhanced selectivity, analytical signaling, and sensitivity after they are modified by nanoparticles or nanomaterials, due to the intrinsic properties of nanoparticles or nanomaterials (e.g. large surface area, good electrical conductivity, unique optical properties, and nanoscale structures) [48,49]. Enzyme-based biosensors with nanoparticles or nanomaterials allow rapid, sensitive, in-time and specific detection of compounds, while traditional detection methods such as chromatography are often difficult for field operations [50], and their testing speed is slow. Several types of nanoparticles/nanomaterials have been selected for the development of biosensors for the detection of target molecules, including gold nanoparticles, silver nanoparticles, carbon nanomaterials, Fe_3O_4 magnetic nanoparticles, platinum particles, and ceria nanospheres. Meanwhile, there have been various enzymes participated in the construction of the biosensors, including GOX, HRP, DNA methyltransferase, protein disulfide isomerase, DNA ligase, organophorous hydrolases, diamine oxidase, human monoamine oxidase B, and nitrate reductase. The reported target molecules for biosensor detection include glucose, cyanide, histamine, pesticides, and enzymes.

There have been several publications focusing on the use of gold nanoparticles for glucose biosensors, which have been applied in the food industry and in biodetection and biomedicine, and have represented a reliable method for glucose detection. Gold nanoparticles improve the performance of glucose biosensor comprising GOX and ZnO nanoarrays [51]. The surface conditions of gold nanoparticles are critical to conformation and bioactivity of immobilized GOX on gold nanoparticle surfaces [52]. The direct electrochemistry of GOX was analyzed after it was immobilized on RGO/silver nanocomposite modified electrode, showing good electrocatalytic activity and sensitivity towards glucose [53]. Ratautas *et al.* [54] explored catalytic oxidation of glucose by glucose dehydrogenase from *Ewingella americana* onto the functionalized gold nanoparticles using 4-mercaptobenzoic acid and 4-aminothiophenol. To obtain a high-performance 3D bioplatfrom for glucose detection, GOX was attached to gold nanoparticles assembled on polyaniline nanowires. The formed entity has good stability and selectivity with a low detection limit of $0.05\ \mu\text{M}$ [55]. Thus, the incorporation of gold nanoparticles can significantly improve the performance of glucose biosensors by surface functionalization, and cooperation with other materials.

In addition to glucose, gold nanoparticles have received considerable attention for the development of biosensors to detect cyanide, enzymes, and genomic DNA (Table 3). A biosensor using HRP and a gold sononanoparticle has been developed for cyanide measurements [56]. The preparation of a GST immunosensor using double-layer gold nanoparticles, GST antibody, and HRP was described by Lu *et al.* [57], showing a minimum detect limit of $0.03\ \text{pg/mL}$. Zhou *et al.* [58] established an electrochemiluminescence biosensor to detect DNA methyltransferase activity based on CdS quantum dots and gold nanoparticles. Gold nanoparticles efficiently enhance the electrochemiluminescence of CdS quantum dots. Another group also achieved the convenient detection of DNA methyltransferase by the cation-exchange reaction of CuS nanoparticles, together with the click chemistry of functionalized gold nanoparticles, without the need for sophisticated instruments [59]. Zheng *et al.* [60] combined citrate-capped gold

nanoparticle probes and dynamic light scattering to develop a method for the examination of the hydrodynamic dimension of protein disulfide isomerase. The hydrodynamic size of the enzyme was deduced based on the change in the average diameter of gold nanoparticles before and after protein corona formation. An electrochemical biosensor that integrated gold nanoparticles, Fe₃O₄ magnetic nanoparticles, DNA ligase and a modified gold electrode was found able to efficiently detect genomic DNA [61].

A number of organophosphorus pesticides (e.g. paraoxon, coumaphos, and parathion) can be decomposed by organophosphorus hydrolases. Large-scale use of organophosphate pesticides has led to a considerable concentration of organophosphates in water and soil. Thus, tools to determine organophosphate levels in the environment are needed urgently. Biosensors based on enzymes and nanoparticles are a good method to monitor them, and have been well practiced. Khaksarinejad *et al.* [62] reported a paraoxon biosensor consisting of organophosphorus hydrolase and silica-coated magnetic nanoparticles with a detection limit of 5×10^{-6} μ M. Via the combination of plant esterase, gold nanoparticles, chitosan, and graphene nanosheets, a biosensor that can detect methyl parathion and malathion was created, where the nanocomposite comprising chitosan, gold nanoparticles, and graphene nanosheets are helpful in the improvement of electron transfer and electric conductivity [63].

The use of nanoparticles and nanomaterials in biosensors has now made it possible to efficiently detect histamine (2-(4-imidazolyl)ethylamine), total monoamines, putrescine (1,4-diaminobutane), and soil nitrate (NO₃⁻). Histamine and putrescine are two amines that are indicators of food quality. Monoamines such as serotonin and dopamine take part in many physiological functions in the human body and are linked to various diseases. As for nitrate, it is a common pollutant in the environment. Detection of these molecules is of importance, because their determination can help assess food quality, contribute to disease diagnosis, or achieve environmental monitoring. To detect histamine, a histamine biosensor was constructed based on the modified carbon screen-printed electrode by diamine oxidase, graphene, platinum particles, and chitosan, which shows low detection limit and good sensitivity [64]. Aigner *et al.* [65] established a monoamine-sensitive electrochemical biosensor with MWCNTs and human monoamine oxidase B. Diamine oxidase was immobilized on ceria nanospheres to measure the putrescine content in tiger prawns [66]. Nitrate reductase was immobilized on epoxy glued silver nanoparticles, leading to the formation of epoxy/AgNPs/NR conjugates for the quantities of soil nitrate [67]. Although nanoparticles and nanomaterials provide many benefits to biosensor performance for measurement of molecules of interest, their environmental risks should be of concern.

Enzymatic Degradation of Nanoparticles or Nanomaterials


The potential adverse impacts of nanoparticles and nanomaterials on the ecosystem require their removal from the environment when their working life is ended. Enzyme degradation is an environmentally friendly technique to degrade nanoparticles or nanomaterials, and has been an area of interest since numerous studies reported the potential toxicity of nanoparticles and nanomaterials to animals, plants and microbes [1,21,68]. Specifically, the enzymatic degradation of CNTs, graphene, and their derivatives have been reviewed recently [1]. HRP [69], lactoperoxidase [70], myeloperoxidase [71], eosinophil peroxidase [72], lignin peroxidase [73], and manganese peroxidase [74] can degrade CNTs and their derivatives, while the main enzymes known for the decomposition of graphene and their derivatives are HRP [75], myeloperoxidase [76], and lignin peroxidase [77] (Table 2). Recently, Chen *et al.* identified the molecular basis of functionalized-triggered SWCNT degradation by HRP and lactoperoxidase [2]. Carboxylation of the substrate resulted in that enzymes bind to substrates more stably, as showed by the enzyme–substrate interaction energies. Different carboxylated

SWCNTs caused significantly different variations in cavity volume of SWCNT-degrading enzymes.

Enzyme Nanoparticles

Interestingly, enzymes can appear in the form of nanoparticles where enzyme molecules aggregate at the nanoscale. In this regard, the interactions between nanoparticles and enzymes are internal; that is, the interactions occur between themselves (Figure 1). To construct a triglyceride bionanosensor, nanoparticles of lipase, glycerol-3-phosphate oxidase, and glycerol kinase were prepared separately, and then were immobilized on an Au electrode [78]. Transmission electron microscopy analyses showed that the average size of lipase, glycerol-3-phosphate oxidase, and glycerol kinase nanoparticle aggregates was 134, 45, and 221 nm, respectively. In another study, the same group also carried out the immobilization of these three types of enzyme nanoparticles (average size: 20 nm) onto a pencil graphite electrode [79]. In addition to the above enzymes, other enzyme nanoparticles were also reported, including cholesterol oxidase, cholesterol esterase [80], and uricase [81].

Available enzyme nanoparticles are often prepared for the construction of biosensors for the determination of molecules of interest, such as triglyceride and uric acid. They have been immobilized onto a variety of electrodes for the improvement of biosensor performance (sensitivity, stability and activity retainment).

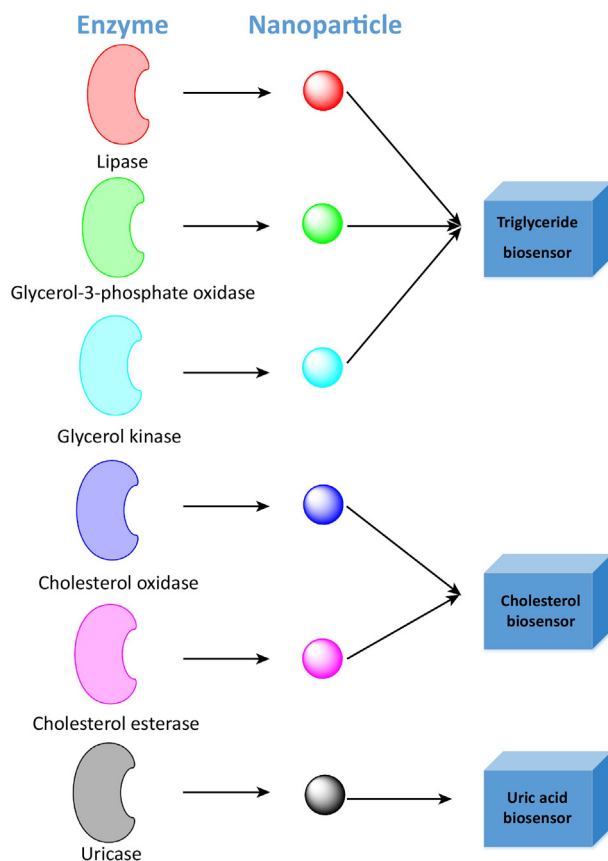

Trends in Biochemical Sciences

Figure 1. Enzyme Nanoparticles for Lipase, Glycerol-3-Phosphate Oxidase, Glycerol Kinase, Cholesterol Oxidase, Cholesterol Esterase, and Uricase.

Enzyme Mimics of Nanoparticles or Nanomaterials

Biological enzymes have been extensively used for industrial activities and environmental remediation. They are efficient in practical applications, but present inherent defects, such as easy inactivation and denaturation [82]. These defects encouraged researchers to create enzyme mimics or nanozymes that have enzyme-like activity and simultaneously overcome the limitations of biological enzymes. Nanoparticles and nanomaterials have received considerable interest in the development of artificial enzymes with improved properties as compared to biological enzymes (e.g. higher resistance to extreme environmental conditions, good stability, low cost, and easy storage) [83]. In this regard, enzymes meet nanoparticles/nanomaterials through the ways that nanoparticles/nanomaterials mimic enzymes and possess catalytic activities. The activity of nanozymes is determined by their own properties, including size, shape, composition, and functionalized molecules [84]. Thus, their activities can be controlled and regulated by designing or changing the properties of nanoparticles or nanomaterials.

The most widely reported nanozymes are peroxidase mimics (Table 3). Polypyrrole nanoparticles present peroxidase-like activity so they can be adopted for the detection of H_2O_2 [3]. Fe_3O_4 nanoparticles are also reported to exhibit peroxidase-like activity through the interconversion of Fe^{2+} and Fe^{3+} . However, the peroxidase-like activity of Fe_3O_4 nanoparticles is limited by multiple factors. Thus, several studies have tried to improve their performance. For example, cubic Fe_3O_4 nanoparticles loaded on supports comprising CNTs and GO nanosheets improve peroxidase-like catalysis activity and electrocatalytic activities compared to those on CNT supports and free Fe_3O_4 nanoparticles, where GO nanosheets enhance the dispersion of CNTs and facilitate the loading of cubic Fe_3O_4 nanocatalysts [82]. Attachment of ATP to Fe_3O_4 nanoparticles improves peroxidase-like activity over a wide range of pH values, allowing them to function even in acid pH [84]. Chitosan-modified AgX (X is Cl, I, or Br) nanoparticles possess peroxidase-like activity in the presence of H_2O_2 or in the case of photoactivation [85]. Stable peroxidase-like activity of porous nanorods of ceria (PN-Ceria) has been reported [86]. PN-Ceria retains stable peroxidase activity at a wide range of temperatures and pH, and has been used as a new diagnostic tool for breast cancer detection. Moreover, many nanoparticles, including platinum nanoparticles [87], gold nanoparticles [88], and carbon nitride nanoparticles modified by Cu^{2+} (Cu^{2+} -g- C_3N_4) [89], also exhibited peroxidase-like activity.

In addition to peroxidase mimics, nanozymes also exhibit other enzyme-like activity. For example, superoxide dismutase (SOD) activity of Gly-Cu(OH)₂ has been reported [90]. Interestingly, some nanoparticles are able to simultaneously show multienzyme activities. Co_3O_4 nanoparticles showed three enzyme-like activities, including peroxidase, catalase, and SOD [91]. These three enzyme-like activities are also observed for Prussian blue nanoparticles [92]. Cu^{2+} -functionalized GO nanoparticles exhibit two enzyme functions; that is, NADH peroxidase and HRP [93].

Concluding Remarks

Here, we reviewed the main pathways by which enzymes meet nanoparticles and nanomaterials, including the enzymatic modification of nanoparticles/nanomaterials, enzymatic immobilization and biosensors with nanoparticles or nanomaterials, enzymatic degradation of nanoparticles or nanomaterials, enzyme nanoparticles, and enzyme mimicry by nanoparticles or nanomaterials (Figure 2). The physicochemical properties of enzymes (e.g. structure) and nanoparticles/nanomaterials (e.g. shape, size, and chemistry) determine the interactional patterns between them. It should be noted, however, new pathways may appear through the development of bionanotechnology.

The main consequence of interactions between enzymes and nanoparticles/nanomaterials is a structural change in the enzymes, accompanied by a decrease or enhancement of enzymatic

Outstanding Questions

What is the underlying mechanism that surface chemistry of nanoparticles and nanomaterials affects their interactions with biological enzymes?


Are there more molecules that can be detected by enzyme-based biosensors with nanoparticles or nanomaterials?

Is it possible to include more types of nanoparticles or nanomaterials for enzymatic immobilization and biosensor development?

Can all enzymes be processed into nanoparticles?

What should be noted when using enzymes to remove environmental nanomaterials in the field conditions?

In addition to those known nanozymes, can nanoparticles and nanomaterials mimic more types of enzymes?

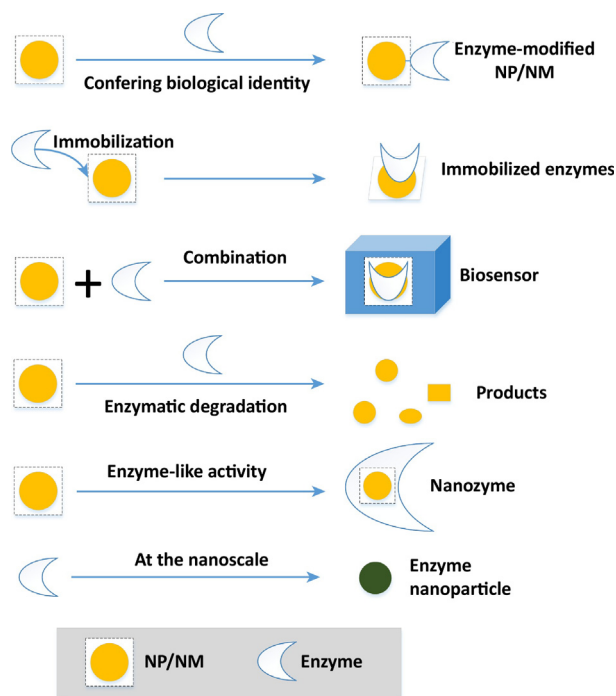

Trends in Biochemical Sciences

Figure 2. Main Pathways by Which Enzymes ‘Meet’ Nanoparticles and Nanomaterials. Abbreviations: NM, nanomaterial; NP, nanoparticle.

activity and stability. Enzymatic immobilization on nanoparticles/nanomaterials can enhance their catalytic performance by rational design and optimization. Their catalytic performance is determined by the properties of both enzymes and nanoparticles/nanomaterials, together with their attached ‘decoration’. Immobilization methods include physical adsorption, covalent modification, and others. Generally, the immobilized enzymes have better thermal stability and reusability, making them able to retain enzymatic activity at a wide range of temperatures and pH than native enzymes. It is important to remember that, among various nanoparticles/nanomaterials, Fe_3O_4 nanoparticles, and gold nanoparticles are two extensively used support materials for enzymatic immobilization. Enzyme–nanoparticle/nanomaterial-based biosensors are another important application of enzyme–nanoparticle/nanomaterial interactions for the detection of numerous molecules. The cooperation between enzymes and nanoparticles/nanomaterials make biosensors endowed with new properties, and thus significantly enhanced the performance of biosensors for the detection of numerous molecules. The negative impacts of nanoparticles and nanomaterials on the environment can be eliminated by enzymatic degradation. Thus, their meeting is ‘hostile’ and results in ‘killing’ one of them. Up to now, there have been limited enzymes available for the degradation of nanoparticles and nanomaterials. The drawbacks of native enzymes have stimulated the emergence of two inventions, enzyme nanoparticles and nanozymes.

A detailed illustration of interactions between enzymes and nanoparticles/nanomaterials will undoubtedly be helpful in understanding the interaction processes, identifying the environmental fate and consequence of nanoparticles and nanomaterials, and better applications of enzyme–nanoparticles for biosensors, other devices or nanocomposites, and biocompatible nanoparticle design. In the future, several key issues need to be overcome (see Outstanding Questions).

(i) Understanding the impacts of nanoparticle surface properties on the interactions of biological enzymes with nanoparticles or nanomaterials and associated underlying mechanism. Studies are needed to investigate the change of biochemical and biophysical properties in enzymes before and after they are in contact with nanoparticles. As demonstrated above, some studies have applied several enzymes to decorate nanoparticles or nanomaterials. However, the information about the interactions between nanoparticles and enzymes is still very limited. Still, there are lots of problems to solve.

(ii) Currently, the variety of molecules that can be detected by enzyme-based biosensors with nanoparticles is limited. Thus, the range of target molecules for biosensor detection needs to be expanded. Moreover, the adopted nanoparticle/nanomaterials and enzymes for biosensors are also limited, given that the number and types of nanoparticles/nanomaterials and enzymes are large.

(iii) In particular, our knowledge on the correlation between nanomaterial/enzyme interactions and health risks is limited. Determining the link between the toxicity of nanoparticles to biology or other effects and interactions between enzymes and nanoparticles/nanomaterials is urgent.

(iv) Identifying general rules that govern the biocompatible and safe nanoparticles or nanomaterials by enzymes.

(v) Constructing algorithms or models for the prediction of behavior and fate of nanoparticles and nanomaterials, by taking into account the available knowledge of interactions of nanoparticle and nanomaterials with enzymes.

Acknowledgments

The study was financially supported by the National Natural Science Foundation of China (51508177, 51521006, 51378190), the Program for Changjiang Scholars and Innovative Research Team in University (IRT-13R17) and the Fundamental Research Funds for the Central Universities.

Resources

BRENDA entries for discussed enzymes

ⁱ<http://www.brenda-enzymes.org/enzyme.php?ecno=3.2.1.17>

ⁱⁱ<http://www.brenda-enzymes.org/enzyme.php?ecno=1.10.3.2>

ⁱⁱⁱ<http://www.brenda-enzymes.org/enzyme.php?ecno=3.8.1.5>

^{iv}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.11.1.14>

^v<http://www.brenda-enzymes.org/enzyme.php?ecno=1.14.12.12>

^{vi}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.11.1.13>

^{vii}<http://www.brenda-enzymes.org/enzyme.php?ecno=3.4.21.1>

^{viii}<http://www.brenda-enzymes.org/enzyme.php?ecno=3.1.3.48>

^{ix}<http://www.brenda-enzymes.org/enzyme.php?ecno=3.1.1.73>

^x<http://www.brenda-enzymes.org/enzyme.php?ecno=3.5.1.14>

^{xi}<http://www.brenda-enzymes.org/enzyme.php?ecno=3.2.1.23>

^{xii}<http://www.brenda-enzymes.org/enzyme.php?ecno=3.1.1.72>

^{xiii}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.1.3.4>

^{xiv}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.10.3.12>

^{xv}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.8.3.1>

^{xvi}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.11.1.7>

^{xvii}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.11.2.2>

^{xviii}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.7.1.2>

^{xix}<http://www.brenda-enzymes.org/enzyme.php?ecno=2.1.1.37>

^{xx}<http://www.brenda-enzymes.org/enzyme.php?ecno=5.3.4.1>

^{xxi}<http://www.brenda-enzymes.org/enzyme.php?ecno=1.1.3.21>

^{xxii}<http://www.brenda-enzymes.org/enzyme.php?ecno=2.7.1.30>

xxiii <http://www.brenda-enzymes.org/enzyme.php?ecno=1.1.3.6>
 xxiv <http://www.brenda-enzymes.org/enzyme.php?ecno=3.1.1.13>
 xxv <http://www.brenda-enzymes.org/enzyme.php?ecno=1.7.3.3>
 xxvi <http://www.brenda-enzymes.org/enzyme.php?ecno=1.15.1.1>
 xxvii <http://www.brenda-enzymes.org/enzyme.php?ecno=3.2.1.41>
 xxviii <http://www.brenda-enzymes.org/enzyme.php?ecno=3.2.1.7>
 xxix <http://www.brenda-enzymes.org/enzyme.php?ecno=3.2.1.1>
 xxx <http://www.brenda-enzymes.org/enzyme.php?ecno=3.2.1.4>
 xxxi <http://www.brenda-enzymes.org/enzyme.php?ecno=3.2.1.22>
 xxxii <http://www.brenda-enzymes.org/enzyme.php?ecno=1.4.3.22>
 xxxiii <http://www.brenda-enzymes.org/enzyme.php?ecno=1.4.3.4>

References

- Chen, M. *et al.* (2017) Biodegradation of carbon nanotubes, graphene, and their derivatives. *Trends Biotechnol.* 9, 836–846
- Chen, M. *et al.* (2017) Understanding enzymatic degradation of single-walled carbon nanotubes triggered by functionalization using molecular dynamics simulation. *Environ. Sci. Nano* 4, 720–727
- Tao, Y. *et al.* (2014) Polypyrrole nanoparticles as promising enzyme mimics for sensitive hydrogen peroxide detection. *Chem. Commun.* 50, 3030–3032
- Shemetov, A.A. *et al.* (2012) Molecular interaction of proteins and peptides with nanoparticles. *ACS Nano* 6, 4585–4602
- Asuri, P. *et al.* (2007) The protein–nanomaterial interface. *Curr. Opin. Biotechnol.* 17, 562–568
- Lynch, I. and Dawson, K.A. (2008) Protein–nanoparticle interactions. *Nano Today* 3, 40–47
- Monopoli, M.P. *et al.* (2012) Biomolecular coronas provide the biological identity of nanosized materials. *Nat. Nanotechnol.* 7, 779–786
- Scheer, M. *et al.* (2011) BRENDA, the enzyme information system in 2011. *Nucleic Acids Res.* 39, D670–D676
- Xu, P. *et al.* (2012) Use of iron oxide nanomaterials in wastewater treatment: a review. *Sci. Total Environ.* 424, 1–10
- Gong, J.-L. *et al.* (2009) Removal of cationic dyes from aqueous solution using magnetic multi-wall carbon nanotube nanocomposite as adsorbent. *J. Hazard. Mater.* 164, 1517–1522
- Lai, C. *et al.* (2016) Synthesis of surface molecular imprinted TiO₂/graphene photocatalyst and its highly efficient photocatalytic degradation of target pollutant under visible light irradiation. *Appl. Surf. Sci.* 390, 368–376
- De Crozals, G. *et al.* (2016) Nanoparticles with multiple properties for biomedical applications: a strategic guide. *Nano Today* 11, 435–463
- Thorkelsson, K. *et al.* (2015) Self-assembly and applications of anisotropic nanomaterials: a review. *Nano Today* 10, 48–66
- Iwashita, K. *et al.* (2016) Arginine suppresses the adsorption of lysozyme onto single-wall carbon nanotubes. *Chem. Lett.* 45, 952–954
- Cedervall, T. *et al.* (2007) Understanding the nanoparticle–protein corona using methods to quantify exchange rates and affinities of proteins for nanoparticles. *Proc. Natl. Acad. Sci. U. S. A.* 104, 2050–2055
- Kelly, P.M. *et al.* (2015) Mapping protein binding sites on the biomolecular corona of nanoparticles. *Nat. Nanotechnol.* 10, 472–479
- Giudice, M.C.L. *et al.* (2016) *In situ* characterization of nanoparticle biomolecular interactions in complex biological media by flow cytometry. *Nat. Commun.* 7, 13475
- Castagnola, V. *et al.* (2017) Towards a classification strategy for complex nanostructures. *Nanoscale Horiz.* 2, 187–198
- Johnson, B.J. *et al.* (2014) Understanding enzymatic acceleration at nanoparticle interfaces: approaches and challenges. *Nano Today* 9, 102–131
- Zhao, X. *et al.* (2015) Influence of the surface functional group density on the carbon-nanotube-induced α -chymotrypsin structure and activity alterations. *ACS Appl. Mater. Interfaces* 7, 18880–18890
- Chen, M. *et al.* (2017) Interaction of carbon nanotubes with microbial enzymes: conformational transitions and potential toxicity. *Environ. Sci. Nano* Published online August 2017. <http://dx.doi.org/10.1039/C7EN00512A>
- Du, P. *et al.* (2014) Adsorption of bovine serum albumin and lysozyme on functionalized carbon nanotubes. *J. Phys. Chem. C* 118, 22249–22257
- Pan, Y. *et al.* (2017) Probing the structural basis and adsorption mechanism of an enzyme on nano-sized protein carriers. *Nano-scale* 9, 3512–3523
- Zhao, D. and Zhou, J. (2016) Electrostatics-mediated α -chymotrypsin inhibition by functionalized single-walled carbon nanotubes. *Phys. Chem. Chem. Phys.* 19, 986–995
- Qian, M. *et al.* (2016) Structural basis of fullerene derivatives as novel potent inhibitors of protein tyrosine phosphatase 1B: insight into the inhibitory mechanism through molecular modeling studies. *J. Chem. Inf. Model.* 56, 2024–2034
- Chen, M. *et al.* (2016) Single-walled carbon nanotube release affects the microbial enzyme-catalyzed oxidation processes of organic pollutants and lignin model compounds in nature. *Chemosphere* 163, 217–226
- Zhang, C. *et al.* (2015) Reduced graphene oxide enhances horseradish peroxidase stability by serving as radical scavenger and redox mediator. *Carbon* 94, 531–538
- Masoud, R. *et al.* (2015) Titanium dioxide nanoparticles increase superoxide anion production by acting on NADPH oxidase. *PLoS One* 10, e0144829
- Rabbani, G. *et al.* (2014) Effect of copper oxide nanoparticles on the conformation and activity of β -galactosidase. *Colloids Surf. B Biointerfaces* 123, 96–105
- He, F. *et al.* (2015) Immobilization of feruloyl esterases on magnetic nanoparticles and its potential in production of ferulic acid. *J. Biosci. Bioeng.* 120, 330–334
- Yang, Y. *et al.* (2016) Robust glucose oxidase with a Fe₃O₄@C-silica nanohybrid structure. *J. Mater. Chem. B* 4, 4726–4731
- Feng, J. *et al.* (2015) Enhancement of the catalytic activity and stability of immobilized aminoacylase using modified magnetic Fe₃O₄ nanoparticles. *Chem. Eng. J.* 286, 216–222
- Saravanakumar, T. *et al.* (2014) Optimized immobilization of peracetic acid producing recombinant acetyl xylan esterase on chitosan coated-Fe₃O₄ magnetic nanoparticles. *Process Biochem.* 49, 1920–1928
- Venditti, I. *et al.* (2015) Bioconjugation of gold-polymer core-shell nanoparticles with bovine serum amine oxidase for biomedical applications. *Colloids Surf. B Biointerfaces* 134, 314–321
- Fournier, E. *et al.* (2016) Creation of a gold nanoparticle based electrochemical assay for the detection of inhibitors of bacterial cytochrome bd oxidases. *Bioelectrochemistry* 111, 109–114
- Alagöz, D. *et al.* (2016) Covalent immobilization and characterization of a novel pullulanase from *Fontibacillus* sp. strain DSHK 107 onto Florisil® and nano-silica for pullulan hydrolysis. *Appl. Biochem. Biotechnol.* 179, 1262–1274

37. Feifel, S.C. *et al.* (2014) Electroactive nanobiomolecular architectures of laccase and cytochrome c on electrodes: applying silica nanoparticles as artificial matrix. *Langmuir* 30, 5363–5367
38. Karimi, M. *et al.* (2016) Immobilization of inulinase from *Aspergillus niger* on octadecyl substituted nanoporous silica: inulin hydrolysis in a continuous mode operation. *Biocatal. Agric. Biotechnol.* 7, 174–180
39. Antony, N. *et al.* (2016) Immobilization of diastase α -amylase on nano zinc oxide. *Food Chem.* 211, 624–630
40. Jang, E. *et al.* (2014) Adsorption of microbial esterases on *Bacillus subtilis*-templated cobalt oxide nanoparticles. *Int. J. Biol. Macromol.* 65, 188–192
41. Zeng, T. *et al.* (2015) Effective electrochemistry of human sulfite oxidase immobilized on quantum-dots-modified indium tin oxide electrode. *ACS Appl. Mater. Interfaces* 7, 21487–21494
42. Tavares, A.P. *et al.* (2015) Laccase immobilization over multi-walled carbon nanotubes: kinetic, thermodynamic and stability studies. *J. Colloid Interface Sci.* 454, 52–60
43. Mubarak, N. *et al.* (2014) Immobilization of cellulase enzyme on functionalized multiwall carbon nanotubes. *J. Mol. Catal. B Enzym.* 107, 124–131
44. Oliveira, S.F. *et al.* (2016) Enzymatic extract containing lignin peroxidase immobilized on carbon nanotubes: potential biocatalyst in dye decolorization. *Saudi J. Biol. Sci.* Published online March 10, 2016. <http://dx.doi.org/10.1016/j.sjbs.2016.1002.1018>
45. Singh, N. *et al.* (2014) Cicer α -galactosidase immobilization onto functionalized graphene nanosheets using response surface method and its applications. *Food Chem.* 142, 430–438
46. Hermanová, S. *et al.* (2015) Graphene oxide immobilized enzymes show high thermal and solvent stability. *Nanoscale* 7, 5852–5858
47. Ansari, S.A. and Husain, Q. (2012) Potential applications of enzymes immobilized on/nano materials: a review. *Biotechnol. Adv.* 30, 512–523
48. Sapountzi, E. *et al.* (2017) Gold nanoparticles assembly on electrospun poly(vinyl alcohol)/poly(ethyleneimine)/glucose oxidase nanofibers for ultrasensitive electrochemical glucose biosensing. *Sens. Actuators B Chem.* 238, 392–401
49. Rocha-Santos, T.A. (2014) Sensors and biosensors based on magnetic nanoparticles. *Trends Anal. Chem.* 62, 28–36
50. Liu, G. *et al.* (2014) Covalent fabrication of methyl parathion hydrolase on gold nanoparticles modified carbon substrates for designing a methyl parathion biosensor. *Biosens. Bioelectron.* 53C, 440–446
51. Zhao, Y. *et al.* (2015) Nanorod arrays composed of zinc oxide modified with gold nanoparticles and glucose oxidase for enzymatic sensing of glucose. *Microchim. Acta* 182, 605–610
52. Song, Y. *et al.* (2015) Conformation, bioactivity and electrochemical performance of glucose oxidase immobilized on surface of gold nanoparticles. *Electrochim. Acta* 158, 56–63
53. Palanisamy, S. *et al.* (2014) Direct electrochemistry and electrocatalysis of glucose oxidase immobilized on reduced graphene oxide and silver nanoparticles nanocomposite modified electrode. *Colloids Surf. B Biointerfaces* 114, 164–169
54. Ratautas, D. *et al.* (2016) High current, low redox potential mediatorless bioanode based on gold nanoparticles and glucose dehydrogenase from *Ewingella americana*. *Electrochim. Acta* 199, 254–260
55. Lou, F. *et al.* (2017) A 3D bio-platform constructed by glucose oxidase adsorbed on Au nanoparticles assembled polyaniline nanowires to sensitively detect glucose by electrochemiluminescence. *J. Electroanal. Chem.* 787, 125–131
56. Attar, A. *et al.* (2015) Amperometric inhibition biosensors based on horseradish peroxidase and gold sononanoparticles immobilized onto different electrodes for cyanide measurements. *Bioelectrochemistry* 101, 84–91
57. Lu, D. *et al.* (2016) A novel glutathione-S transferase immunosensor based on horseradish peroxidase and double-layer gold nanoparticles. *Biomed. Microdevices* 18, 1–9
58. Zhou, H. *et al.* (2016) Efficient enhancement of electrochemiluminescence from cadmium sulfide quantum dots by glucose oxidase mimicking gold nanoparticles for highly sensitive assay of methyltransferase activity. *Anal. Chem.* 88, 2976–2983
59. Zhang, X. *et al.* (2016) Visual detection of single-nucleotide polymorphisms and DNA methyltransferase based on cation-exchange of CuS nanoparticles and click chemistry of functionalized gold nanoparticles. *Chem. Commun.* 52, 13261–13264
60. Zheng, T. *et al.* (2016) A simple and fast method to study the hydrodynamic size difference of protein disulfide isomerase in oxidized and reduced form using gold nanoparticles and dynamic light scattering. *Analyst* 141, 934–938
61. Husharian, R. *et al.* (2015) Facilitating the indirect detection of genomic DNA in an electrochemical DNA biosensor using magnetic nanoparticles and DNA ligase. *Anal. Chem. Res.* 6, 17–25
62. Khaksarnejad, R. *et al.* (2015) An organophosphorus hydrolase-based biosensor for direct detection of paraoxon using silica-coated magnetic nanoparticles. *Appl. Biochem. Biotechnol.* 176, 359–371
63. Bao, J. *et al.* (2015) Plant esterase–chitosan/gold nanoparticles–graphene nanosheet composite-based biosensor for the ultra-sensitive detection of organophosphate pesticides. *J. Agric. Food Chem.* 63, 10319–10326
64. Apetrei, I.M. and Apetrei, C. (2016) Amperometric biosensor based on diamine oxidase/platinum nanoparticles/graphene/chitosan modified screen-printed carbon electrode for histamine detection. *Sensors-Basel* 16, 422
65. Aigner, M. *et al.* (2017) Determination of total monoamines in rat brain via nanotubes based human monoamine oxidase B biosensor. *Electroanalysis* 29, 367–373
66. Gumpu, M.B. *et al.* (2016) Determination of putrescine in tiger prawn using an amperometric biosensor based on immobilization of diamine oxidase onto ceria nanospheres. *Food Bioprocess. Technol.* 9, 717–724
67. Sachdeva, V. and Hooda, V. (2015) Immobilization of nitrate reductase onto epoxy affixed silver nanoparticles for determination of soil nitrates. *Int. J. Biol. Macromol.* 79, 240–247
68. Chen, M. *et al.* (2017) Interactions of carbon nanotubes and/or graphene with manganese peroxidase during biodegradation of endocrine disruptors and triclosan. *Chemosphere* 184, 127–136
69. Flores-Cervantes, D.X. *et al.* (2014) Slow biotransformation of carbon nanotubes by horseradish peroxidase. *Environ. Sci. Technol.* 48, 4826–4834
70. Bhattacharya, K. *et al.* (2015) Lactoperoxidase-mediated degradation of single-walled carbon nanotubes in the presence of pulmonary surfactant. *Carbon* 91, 506–517
71. Kagan, V.E. *et al.* (2010) Carbon nanotubes degraded by neutrophil myeloperoxidase induce less pulmonary inflammation. *Nat. Nanotechnol.* 5, 354–359
72. Andón, F.T. *et al.* (2013) Biodegradation of single-walled carbon nanotubes by eosinophil peroxidase. *Small* 9, 2721–2729
73. Chandrasekaran, G. *et al.* (2014) Oxidative biodegradation of single-walled carbon nanotubes by partially purified lignin peroxidase from *Sparassis latifolia* mushroom. *J. Ind. Eng. Chem.* 20, 3367–3374
74. Zhang, C. *et al.* (2014) Manganese peroxidase degrades pristine but not surface-oxidized (carboxylated) single-walled carbon nanotubes. *Environ. Sci. Technol.* 48, 7918–7923
75. Li, Y. *et al.* (2014) Surface coating-dependent cytotoxicity and degradation of graphene derivatives: towards the design of non-toxic, degradable nano-graphene. *Small* 10, 1544–1554
76. Kurapati, R. *et al.* (2015) Dispersibility-dependent biodegradation of graphene oxide by myeloperoxidase. *Small* 11, 3985–3994
77. Lalwani, G. *et al.* (2014) Enzymatic degradation of oxidized and reduced graphene nanoribbons by lignin peroxidase. *J. Mater. Chem. B* 2, 6354–6362
78. Pundir, C. and Aggarwal, V. (2017) Amperometric triglyceride biosensor based on nanoparticles of lipase, glycerol kinase, glycerol-3-phosphate oxidase. *Anal. Biochem.* 517, 56–63
79. Narwal, V. and Pundir, C. (2017) An improved amperometric triglyceride biosensor based on co-immobilization of nanoparticles of lipase, glycerol kinase and glycerol 3-phosphate oxidase onto pencil graphite electrode. *Enzyme Microb. Technol.* 100, 11–16

80. Aggarwal, V. *et al.* (2016) Amperometric determination of serum total cholesterol with nanoparticles of cholesterol esterase and cholesterol oxidase. *Anal. Biochem.* 500, 6–11
81. Chauhan, N. *et al.* (2014) Construction of an uricase nanoparticles modified Au electrode for amperometric determination of uric acid. *Appl. Biochem. Biotechnol.* 174, 1683–1694
82. Wang, H. *et al.* (2014) Recyclable enzyme mimic of cubic Fe_3O_4 nanoparticles loaded on graphene oxide-dispersed carbon nanotubes with enhanced peroxidase-like catalysis and electrocatalysis. *J. Mater. Chem. B* 2, 4442–4448
83. Fan, Y. *et al.* (2014) Mesoporous material-based manipulation of the enzyme-like activity of CoFe_2O_4 nanoparticles. *J. Mater. Chem. A* 2, 2482–2486
84. Vallabani, N.S. *et al.* (2017) ATP-mediated intrinsic peroxidase-like activity of Fe_3O_4 -based nanozyme: one step detection of blood glucose at physiological pH. *Colloids Surf. B Biointerfaces* 153, 52–60
85. Wang, G.-L. *et al.* (2014) Dual responsive enzyme mimicking activity of AgX ($\text{X} = \text{Cl}, \text{Br}, \text{I}$) nanoparticles and its application for cancer cell detection. *ACS Appl. Mater. Interfaces* 6, 6434–6442
86. Tian, Z. *et al.* (2015) Highly sensitive and robust peroxidase-like activity of porous nanorods of ceria and their application for breast cancer detection. *Biomaterials* 59, 116–124
87. Chen, W. *et al.* (2017) DNA-mediated inhibition of peroxidase-like activities on platinum nanoparticles for simple and rapid colorimetric detection of nucleic acids. *Biosens. Bioelectron.* 94, 169–175
88. Ahmed, S.R. *et al.* (2016) Detection of influenza virus using peroxidase-mimic of gold nanoparticles. *Biotechnol. Bioeng.* 113, 2298–2303
89. Vázquez-González, M. *et al.* (2017) Mimicking horseradish peroxidase functions using Cu^{2+} -modified carbon nitride nanoparticles or Cu^{2+} -modified carbon dots as heterogeneous catalysts. *ACS Nano* 11, 3247–3253
90. Korschelt, K. *et al.* (2017) Glycine-functionalized copper (II) hydroxide nanoparticles with high intrinsic superoxide dismutase activity. *Nanoscale* 9, 3952–3960
91. Dong, J. *et al.* (2014) Co_3O_4 nanoparticles with multi-enzyme activities and their application in immunohistochemical assay. *ACS Appl. Mater. Interfaces* 6, 1959–1970
92. Zhang, W. *et al.* (2016) Prussian blue nanoparticles as multi-enzyme mimetics and reactive oxygen species scavengers. *J. Am. Chem. Soc.* 138, 5860–5865
93. Wang, S. *et al.* (2017) Mimicking horseradish peroxidase and NADH peroxidase by heterogeneous Cu^{2+} -modified graphene oxide nanoparticles. *Nano Lett.* 17, 2043–2048