


Adsorption of DNA Oligonucleotides by Titanium Dioxide Nanoparticles

Xu Zhang,^{†,‡} Feng Wang,[†] Biwu Liu,[†] Erin Y. Kelly,[†] Mark R. Servos,[‡] and Juewen Liu^{*,†}

[†]Department of Chemistry and Waterloo Institute for Nanotechnology, and [‡]Department of Biology, University of Waterloo, 200 University Avenue West, Waterloo, Ontario N2L 3G1, Canada

S Supporting Information

ABSTRACT: Titanium dioxide (TiO₂) or titania shows great promise in detoxification and drug delivery. To reach its full potential, it is important to interface TiO₂ with biomolecules to harness their molecular recognition function. To this end, DNA attachment is an important topic. Previous work has mainly focused on long double-stranded DNA or single nucleotides. For biosensor development and targeted drug delivery, it is more important to use single-stranded oligonucleotides. Herein, the interaction between fluorescently labeled oligonucleotides and TiO₂ nanoparticles is reported. The point of zero charge (PZC) of TiO₂ is around 6 in water or acetate buffer; therefore, the particles are positively charged at lower pH. However, if in phosphate or citrate buffer, the particles are negatively charged, even at pH ~2, suggesting strong adsorption of buffer anions. DNA adsorption takes place mainly via the phosphate backbone, although the bases might also have moderate contributions. Peptide nucleic acids (PNAs) with an amide backbone cannot be adsorbed. DNA adsorption is strongly affected by inorganic anions, where phosphate and citrate can strongly inhibit DNA adsorption. DNA adsorption is promoted by adding salt or lowering pH. DNA adsorption is accompanied with fluorescence quenching, and double-stranded DNA showed reduced quenching, allowing for the detection of DNA using TiO₂ nanoparticles.

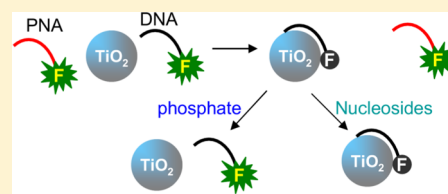

INTRODUCTION

Titanium dioxide (TiO₂) or titania is an important industrial material for a diverse range of applications, where it is best known as a white pigment. It is also used in sunscreens and food additives, suggesting its excellent biocompatibility.^{1–3} Indeed, a number of assays confirm that even relatively high concentrations (e.g., 0.2 mg/mL) of titania do not show noticeable toxicity to cells and animals.⁴ This makes titania a useful vehicle for drug delivery.⁵ At the same time, TiO₂ is a photocatalyst widely explored for water detoxification and disinfection under light exposure.⁶ Attaching affinity ligands to its surface can improve specificity to selectively kill cancer or bacterial cells.⁷

In comparison to the vast amount of work on gold, carbon, or silica nanoparticles (NPs),^{8–13} functionalization of titania with biomolecules is reported only in a few cases. For example, antibodies were physisorbed to target cancer cells.^{14,15} To achieve covalent attachment, Brook and co-workers used the sol–gel chemistry to graft a layer of amino-modified silane on titania, upon which biotin or protein was coupled.^{7,16,17} Levina et al. considered that titania is negatively charged at neutral pH. They prepared a DNA/polylysine conjugate, where the positively charged polylysine is used to anchor onto the titania surface and the DNA fragment can hybridize to its complementary strand.^{18,19}

To make the attachment chemistry more cost-effective, it is desirable to directly adsorb non-modified DNA. Zhu et al. studied the adsorption of calf thymus DNA by TiO₂ NPs, and they concluded that phosphate is responsible for DNA

adsorption based on infrared (IR) spectroscopy.²⁰ Suzuki et al. used sonication to assist the adsorption of salmon testes DNA, which is also a long double-stranded DNA (dsDNA).²¹ They found that the DNA adsorbed very tightly and did not desorb, even by heating at 56 °C for several hours. Desorption occurred only at 98 °C in pH 14 solution. In addition to the previously proposed phosphate binding, the authors suspected that adsorption might also take place by electrostatic interaction at acidic pH (where the surface of TiO₂ is positively charged) or by bridging cations. This adsorption reaction was used to precipitate TiO₂ NPs for environmental remediation.²² The authors further increased DNA loading capacity by lowering the buffer pH to 2, which was attributed to the reduced electrostatic repulsion between DNA and the particle surface.²³ Cleaves et al. studied the adsorption of several DNA/RNA bases, nucleosides, and monophosphate nucleotides, where they concluded that nucleotides adsorbed more tightly than nucleobases.²⁴ They further noticed that cytosine was adsorbed significantly more at lower pH, while adenine and uracil was less affected. Thus far, it is not conclusive whether DNA adsorption to titania is achieved via the bases or the phosphate backbone.

All of the previous work suggested that both long dsDNA and single nucleobases/nucleotides can be adsorbed by TiO₂ NPs. For analytical and biomedical applications, it is more

Received: December 1, 2013

Revised: January 3, 2014

Published: January 4, 2014



Table 1. DNA and PNA Used in This Work

DNA name	sequence (5' → 3') and modification
FAM-DNA1	FAM-TTCTTTCTTCCCCTGTTTGT
cDNA1	AACAAACAAGGGGAAGAAAGAA
T ₁₅	TTTTTTTTTTTTTTTTT
FAM-A ₁₅	FAM-AAAAAAAAAAAAAAAAA
FAM-C ₁₅	FAM-CCCCCCCCCCCCCCC
FAM-G ₁₅	FAM-GGGGGGGGGGGGGGG
FAM-T ₁₅	FAM-TTTTTTTTTTTTTTTTT
FAM-A ₃₀	FAM-AAAAAAAAAAAAAAAAAAAAAAAAA
FAM-A ₄₅	FAM-AAAAAAAAAAAAAAAAAAAAAAAAAAAAAAAAA
Cy3-T ₁₅	Cy3-TTTTTTTTTTTTTTTTT
PNA	FAM-CACTGACCTGGG

desirable to attach single-stranded DNA (ssDNA) oligonucleotides with well-defined sequences, such as aptamers.^{8–13,25} Using oligonucleotide probes also allows for systematic studies on the effect of DNA sequence and length. We previously employed oligonucleotide probes to study their interaction with gold,^{26,27} graphene oxide,²⁸ coordination polymers,²⁹ and nanoceria.³⁰ In this paper, we report the surface interaction of short ssDNA on TiO₂ NPs.

MATERIALS AND METHODS

Chemicals. All of the DNA samples were purchased from Integrated DNA Technologies (IDT, Coralville, IA) and were purified by standard desalting. The peptide nucleic acid (PNA) sample was purchased from Biosynthesis, Inc. (Lewisville, TX), and the stock was dissolved in 0.1% trifluoroacetic acid. The sequences of DNA used in this work are shown in Table 1. TiO₂ NPs (catalog number 718467) were purchased from Sigma-Aldrich. Sodium phosphate, sodium citrate, 4-(2-hydroxyethyl)-1-piperazineethanesulfonic acid (HEPES), sodium acetate, sodium nitrate, and all of the ribonucleosides were from Mandel Scientific (Guelph, Ontario, Canada). Milli-Q water was used for all of the experiments.

DLS Measurement. ζ potential was measured on a Malvern instrument (Zetasizer Nano 90) using the dip-cell setup. In a typical experiment, TiO₂ NPs (final concentration of 0.72 nM) were dispersed in 1 mL of water or buffer. The typical buffer concentration was 10 mM phosphate, citrate, HEPES, or acetate. The pH values were adjusted by gradually adding NaOH or HCl. The temperature was set at 25 °C.

DNA Adsorption Assays. The diameter of our TiO₂ NP is ~20 nm [supplied by the vendor and also from transmission electron microscopy (TEM)]. Assuming a spherical shape and density of 4.23 g/cm³, 1% TiO₂ has a NP molar concentration of 940 nM. In a typical experiment to measure DNA adsorption kinetics, 1 μ L of 1 μ M FAM-labeled DNA (FAM = 6-carboxyfluorescein) stock solution (final concentration of 10 nM) and 2 μ L of 3 M NaCl (final concentration of 60 mM) were mixed in 95 μ L of HEPES buffer (5 mM, pH 7.6) in a 96-well plate. Next, the fluorescence signal baseline (excitation at 485 nm and emission at 535 nm) was measured for 1 min under the kinetic mode using a plate reader (Tecan Infinite F200Pro) prior to a quick addition and mixing of 2 μ L of 45 nM TiO₂ NPs (final TiO₂ NP concentration of 0.9 nM). Afterward, the fluorescence intensity at 535 nm was monitored for 45 min to track the adsorption kinetics. The concentration of NaCl was varied in the salt-dependent experiments (NaCl = 0, 30, 60, 90, and 120 mM). In the same way, the effect of other anions (NaNO₃, NaOAc, Na₃citrate, and Na₂HPO₄) on DNA adsorption was studied. For these assays, the concentration of Na⁺ was maintained constant (60 mM), so that the concentration of the anions was different (e.g., [citrate] = 20 mM, and [SO₄²⁻] = 30 mM). For PNA adsorption, the FAM-labeled PNA concentration was 14 nM with 60 mM NaCl.

DNA Loading Capacity. The loading capacity of DNA was measured by the difference of the fluorescence intensity of each sample

before and after the addition of TiO₂ NPs for DNA adsorption. The DNA loading under neutral and pH 2 conditions was studied. Under neutral pH, various concentrations of FAM-A₁₅ (0.1, 0.2, 0.5, 1, and 2 μ M) were mixed with 10 nM TiO₂ in 5 mM HEPES buffer (pH 7.6 with 60 mM NaCl). The total volume was 100 μ L for each sample (n = 3). After overnight incubation under room temperature, the sample solutions were centrifuged and the supernatant fluorescence intensity was measured to quantify adsorbed DNA. For the acidic condition, 2 μ L of 0.5 M HCl solution was added to 90 μ L of Milli-Q water before mixing with a small volume of DNA stock solution (100 μ M) and 2.7 μ L of TiO₂ solution (360 nM) in water at room temperature for 3 min. Afterward, the mixture was sonicated for 2 min in a sonication bath prior to a 5 min centrifugation (15 000 rpm) to precipitate the TiO₂ NPs. To monitor the fluorescence intensity of the supernatant, the same volume of NaOH (0.01 M) was added to 50 mM HEPES buffer to adjust the pH to neutral. This is important because the FAM fluorescence is a strong function of pH. Care was taken for developing calibration curves, where the same concentration of Na⁺ (using NaCl) was added to the standard solution to maintain a consistent ionic strength.

DNA Desorption. To investigate the displacement of adsorbed DNA, the DNA/TiO₂ nanoconjugate was prepared using the pH 2 method to achieve fast and high loading capacity. After three rounds of rinsing with pure water to remove the loosely adsorbed DNA, the conjugate was dispersed in water, with the TiO₂ concentration being 10 nM. Then, 5 μ L of the conjugate was transferred into 90 μ L of 5 mM HEPES (pH 7.6) to measure the fluorescence baseline for 2 min before a quick addition of 5 μ L of phosphate solution of various concentrations to make the final concentration of phosphate be 0, 0.2, 2, or 20 mM. The fluorescence was monitored for 40 min. The possible displacement of adsorbed DNA by 5 mM nucleosides was also studied (adenosine, guanosine, cytidine, and uridine), where 10 μ L of nucleoside solution (50 mM) was added to the conjugate solution and incubated for 30 min before measuring the fluorescence intensity.

DNA Detection. To study the adsorption kinetics of ssDNA and dsDNA, FAM-DNA1 and its cDNA were first hybridized by mixing 10 nM of FAM-DNA1 with various concentrations of cDNA1 or a non-complementary strand (T₁₅, 20 nM) in 10 mM HEPES (pH 7.6, with 150 mM NaCl). These solutions were heated to 90 °C and then slowly cooled to room temperature for DNA hybridization. After monitoring background fluorescence for 6 min, TiO₂ NP (final concentration of 0.9 nM) was added to each sample and the fluorescence was measured for 1 h.

Fluorescence Quenching by TiO₂ NPs. To illustrate the fluorescence quenching capability of TiO₂ NPs, we compared the fluorescence of four samples: (1) free Cy3-T₁₅, (2) Cy3-T₁₅ adsorbed on TiO₂, (3) free FAM-T₁₅, and (4) FAM-T₁₅ adsorbed on TiO₂. The concentration for DNA was 0.5 μ M, and that for TiO₂ NPs was 10 nM. Samples 2 and 4 were prepared following the pH 2 procedure described in the last section, with the ratio of initial concentrations of DNA/TiO₂ NP = 50. The conjugates were rinsed twice with pure water to remove the free DNAs and excited using Safe Imager 2.0 Blue Light Transilluminator (Invitrogen).

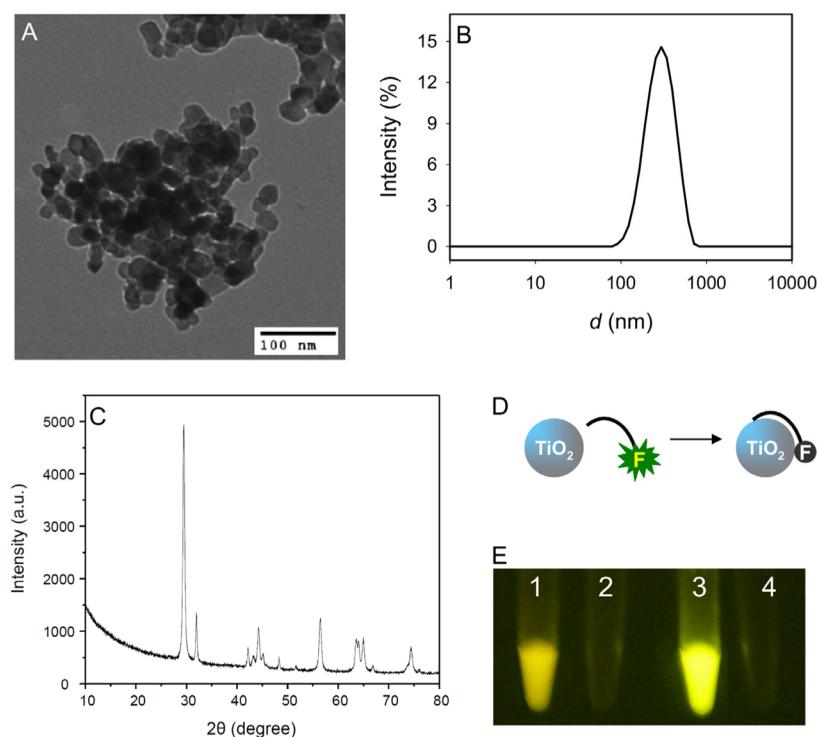


Figure 1. (A) TEM, (B) DLS, and (C) XRD of the TiO_2 NP samples used in this work. (D) Schematics of fluorescently labeled DNA adsorption by TiO_2 NPs and fluorescence quenching. (E) Fluorescence photograph showing tube 1, free Cy3- T_{15} ; tube 2, Cy3- T_{15} adsorbed by TiO_2 NPs; tube 3, free FAM- T_{15} ; and tube 4, FAM- T_{15} adsorbed by TiO_2 NPs.

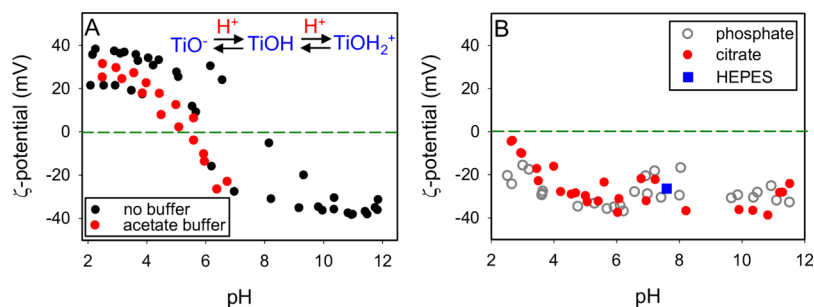


Figure 2. ζ potential of TiO_2 NP as a function of pH in (A) water and acetate buffers or (B) phosphate, citrate, and HEPES buffers. (Inset of panel A) Change of the surface charge through protonation for the native TiO_2 surface.

RESULTS AND DISCUSSION

Surface Properties of TiO_2 NPs. The size of our TiO_2 NPs is ~ 20 nm under TEM (Figure 1A). Because we intend to probe the native surface of TiO_2 , no capping agent or surfactant was used. When dispersed in water at around neutral pH, the surface charge of TiO_2 is close to zero (*vide infra*). For these reasons, the particles were aggregated. Dynamic light scattering (DLS) shows an average size of ~ 300 nm, which agrees with aggregation of TiO_2 NPs (Figure 1B). More DLS data of the particles in different buffer conditions are shown in Figure S1 of the Supporting Information. X-ray diffraction (XRD) shows that the particles are crystalline and have the anatase phase (Figure 1C).

Because DNA is a negatively charged polymer, electrostatic interactions are often important for its adsorption. To understand the surface charge of TiO_2 NPs, we first measured ζ potential in water without buffer and adjusted pH by HCl or NaOH (black dots in Figure 2A). The particles are negatively charged at pH greater than 7 and positively charged at pH

lower than 6. This is consistent with literature reports on TiO_2 NPs prepared by various methods.³¹ The reactions responsible for its surface charging are shown in the inset of Figure 2A.³² The data points are quite scattered around neutral pH because this sample was not buffered. Adding 20 mM acetate buffer has improved the quality of the data, and a similar pH-dependent surface charge inversion was also observed around pH 6 (red dots in Figure 2A). To buffer over a wider range of pH, we also measured ζ potential in phosphate and citrate buffers (Figure 2B), where the surface remained negative in all tested pH values. It is likely that the TiO_2 surface has affinity for the oxygen groups in the phosphate and citrate anions.³³ Adsorption of these anions rendered a negatively charged surface, regardless of pH, which might have an adverse effect for DNA adsorption. We performed most of our experiments in pH 7.6 HEPES, and the surface is negatively charged under this condition (blue square in Figure 2B).

DNA Adsorption. After understanding the surface charge of TiO_2 NPs, DNA adsorption was studied. First, we need to develop an assay to follow DNA adsorption. Because many

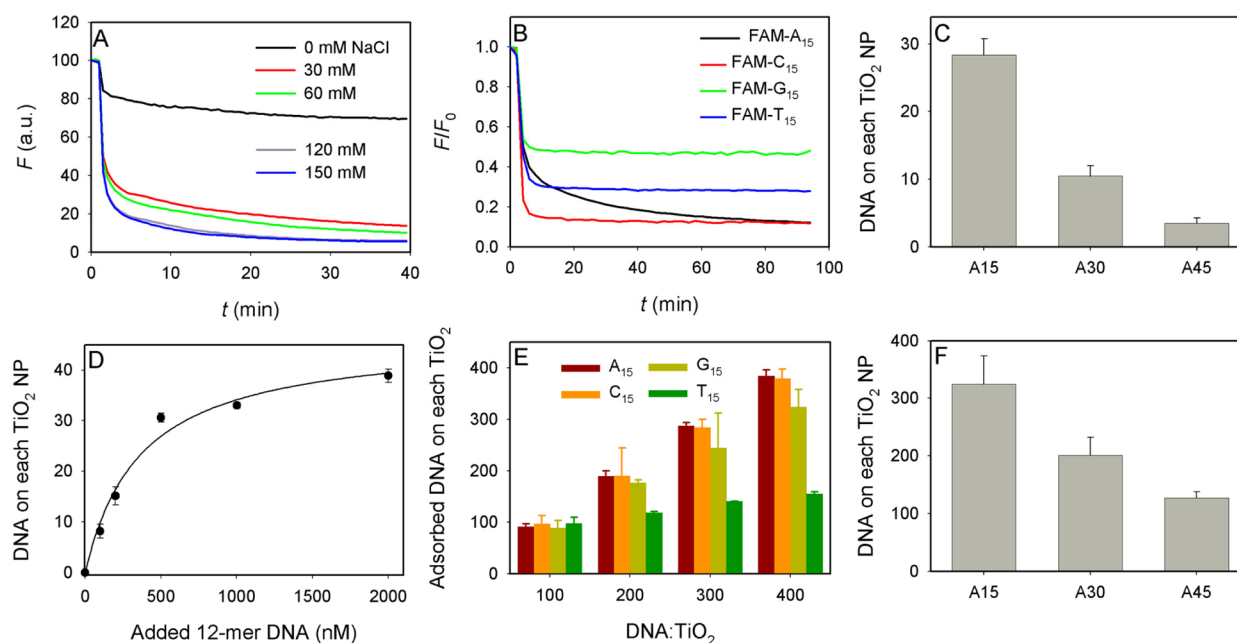


Figure 3. (A) Adsorption of FAM-A₁₅ as a function of the NaCl concentration in 5 mM HEPES buffer. (B) Adsorption kinetics of various DNA sequences. (C) DNA adsorption capacity at pH 7.6 as a function of the DNA length. (D) DNA adsorption isotherm at pH 7.6. (E) DNA adsorption capacity at pH 2. (F) DNA adsorption capacity at pH 2 as a function of the DNA length.

inorganic surfaces quench adsorbed fluorophores (e.g., carbon nanotubes,³⁴ graphene oxide,^{35,36} gold,³⁷ nanoceria,³⁰ and quantum dots³⁸), we tested whether TiO₂ NPs also have such an effect. Figure 1E shows a fluorescence photograph that both FAM- and Cy3-labeled DNA are almost fully quenched by TiO₂ NPs. This also indicates that DNA oligonucleotides are adsorbed (Figure 1D). TiO₂ is a large band gap semiconductor and might accept electrons from excited fluorophores to quench its fluorescence.

Because phosphate and citrate can be adsorbed by TiO₂ NPs and may cause artifacts for studying DNA adsorption, we chose to use HEPES buffer (pH 7.6) for most of our experiments. The unmodified TiO₂ surface carries a negative charge in pH 7.6 HEPES buffer (Figure 2B). Therefore, to adsorb negatively charged DNA, salt should be important to screen charge repulsion. To test this, we measured FAM-labeled A₁₅ DNA adsorption as a function of the NaCl concentration (Figure 3A). Indeed, little adsorption was observed in the absence of salt, and the rate of adsorption was significantly enhanced with more than 30 mM NaCl. Next, we measured the adsorption of 15-mer DNA homopolymers in the presence of 60 mM NaCl (Figure 3B). These DNAs showed slightly different adsorption behaviors. For example, A₁₅ adsorption continued to occur in 90 min, while the other three DNA reached a stable fluorescence quite rapidly. The amount of fluorescence quenching (i.e., adsorption) was the least for G₁₅. This might be attributed to DNA secondary structures affecting the adsorption kinetics. For example, poly-G DNA tends to form quadruplex structures, which may hinder adsorption.

Next, we tested the effect of the DNA length (Figure 3C), where the capacity dropped significantly as the length of DNA increased. This suggests that the DNA wraps around TiO₂ NPs, instead of adopting an upright conformation. This capacity is, however, quite low if we compare it to gold NPs of the same size; each gold NP adsorbs ~200 thiolated DNA with an upright conformation.³⁹ Using a random sequenced 12-mer DNA, we measured DNA adsorption capacity as a function of

the initial DNA concentration (Figure 3D), and our data fit to a Langmuir isotherm. This suggests that there is an adsorption/desorption equilibrium in our system, and it is also reasonable that DNA adsorption on TiO₂ NP stops at a monolayer. It is quite striking that the capacity becomes much higher when DNA was loaded at pH 2 (Figure 3E). For example, at a DNA/TiO₂ ratio of 100:1, DNA was quantitatively adsorbed for all of the tested sequences. Close to complete adsorption was achieved also for A₁₅ and C₁₅ at up to a 400:1 ratio, while the capacity was slightly lower for G₁₅ and much lower for T₁₅. On the other hand, at neutral pH, the A₁₅ loading was less than 30 (Figure 3C). At pH 2, the TiO₂ surface is positively charged and may attract DNA via electrostatic interactions. The negative charges on DNA are from the backbone phosphate, which has a pK_a value close to 2. However, protonated phosphate might not bind to the TiO₂ surface. We reason that the different capacity at pH 2 is likely due to the different pK_a values of the bases. T₁₅ cannot be protonated, even at pH 2, and thus, the thymine base does not contribute electrostatically for T₁₅ DNA adsorption, limiting its capacity to ~100 DNA per particle. Guanine has a pK_a of 2.2 and, therefore, can be partially protonated at pH 2. The pK_a values for adenine and cytosine are 3.5 and 4.2, respectively, and can be fully protonated at pH 2. This trend matches with our data, and thus, the ultrahigh capacity of these DNA is related to both protonation of the particle and DNA bases. At pH 2, the loading capacity also decreased with increasing DNA length. Nevertheless, the 30-mer DNA was still loaded at ~200 per TiO₂ NP (Figure 3F). Note that each 20 nm gold NP can only adsorb ~180 thiolated 25-mer DNA, where DNA has an upright conformation.³⁹ Therefore, to load a similar density of DNA onto TiO₂, it is unlikely that each DNA wraps around the particles. More likely, the DNAs are adsorbed via only one or a few nucleotides. Such high DNA loading at low pH is consistent with the report by Suzuki et al.,²³ who used long dsDNA in their study. Here, we provide more detailed insight regarding the effect of different DNA sequences, where base

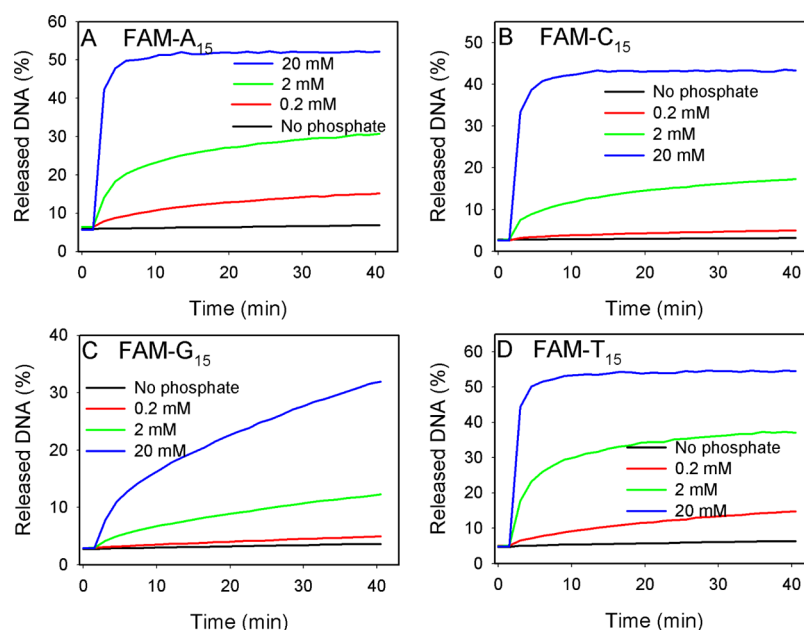


Figure 4. Kinetics of FAM-labeled (A) A₁₅, (B) C₁₅, (C) G₁₅ and (D) T₁₅ DNA desorption induced by adding various concentrations of phosphate buffer.

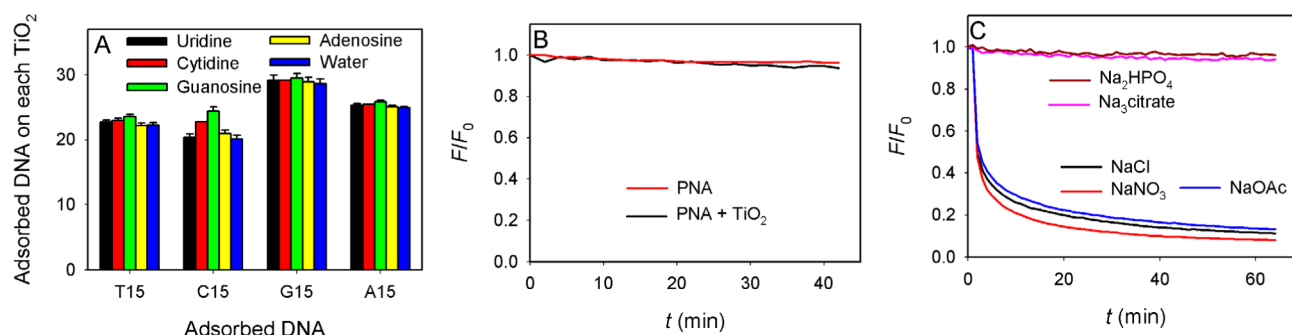


Figure 5. (A) DNA adsorption capacity in the presence of 5 mM various ribonucleosides. The fact that the capacity is similar for all of the samples indicates that DNA bases only played a very limited role in contributing to DNA adsorption. (B) FAM-labeled PNA does not adsorb on TiO₂. (C) FAM-labeled DNA adsorption in buffers containing various salts. Na⁺ = 60 mM, and the anion concentration is adjusted accordingly. A large drop in fluorescence indicates effective DNA adsorption.

protonation appears to be important. Such pH-dependent DNA loading was also observed for gold and silver NPs^{26,27,40,41} and graphene oxide.⁴²

Desorption and Displacement. The above studies were carried out in HEPES buffer. Because TiO₂ appears to strongly adsorb phosphate based on our ζ -potential measurement (Figure 2B), we next measured DNA adsorption/desorption in other buffers. An important question is whether DNA adsorption is achieved via the bases or the phosphate backbone. Previous studies have not systematically addressed this question. We herein probed it using displacement reactions. In our hypothesis, if adsorption is through the backbone phosphate, the adsorbed DNA might be displaced by adding free phosphate. To test this, we loaded the four different DNAs and added various concentrations of phosphate buffer (pH 7.4). As shown in Figure 4, all of the DNA sequences showed time-dependent fluorescence enhancement and a higher concentration of phosphate gave a faster signal increase. Therefore, the DNA phosphate backbone is likely to play an important role in its adsorption. At the same time, the kinetics of FAM-G₁₅ is the slowest, while all of the other three DNAs showed similarly fast desorption. Therefore, it cannot be ruled out that the guanine

base might also have some affinity for the TiO₂ NP surface as well. Interestingly, Cleaves et al. concluded that the strength of nucleotide adsorption follows the order of G > C > U > A,²⁴ which agrees with our data that the poly-G DNA desorbed the slowest. Again, it needs to be emphasized that phosphate adsorption plays the major role. Phosphate-induced desorption also indicates that longer DNA is adsorbed slightly more tightly (see Figure S2 of the Supporting Information), which is consistent with the lower capacity of the longer DNA (Figure 3F). In other words, lower capacity means more contacting points for each DNA and stronger affinity.

We next used nucleosides for displacement. In this experiment, DNA-loaded TiO₂ NPs were mixed with 5 mM adenosine, cytidine, guanosine, or uridine. After incubation for 30 min, the DNA remaining on the particles was quantified (Figure 5A). All of the samples showed similar DNA loading as the control without any treatment. Therefore, DNA adsorption should occur mainly via the backbone phosphate, instead of the bases. As a further control, a FAM-labeled PNA was added, and no adsorption was observed (Figure 5B). In a PNA, the amide backbone replaces the phosphate backbone in DNA, while the bases are the same. The lack of PNA adsorption further

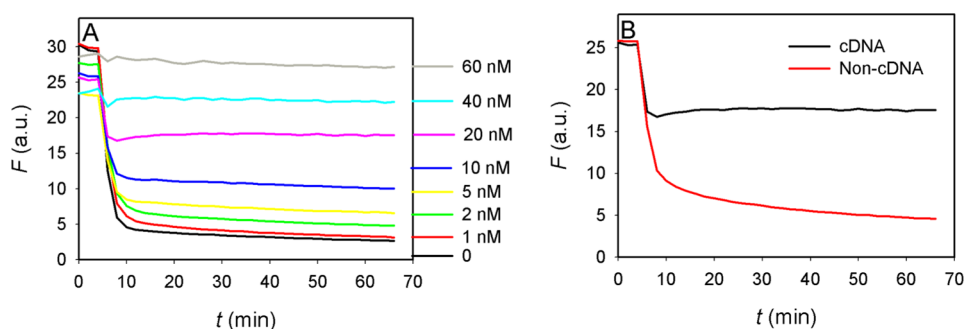


Figure 6. (A) Response of a FAM-labeled probe DNA hybridized with various concentrations of its cDNA after mixing with TiO_2 NPs. The higher fluorescence signal with more cDNA indicates that the fluorescence in a dsDNA is less effectively quenched. (B) For a non-complementary DNA, the response is more similar to that for the free probe DNA, suggesting high specificity. The probe DNA concentration is 10 nM, and the cDNA concentration in panel B is 20 nM. The TiO_2 NP concentration is 0.9 nM.

confirms the phosphate adsorption mechanism; adsorption by the bases in the absence of phosphate was too weak.

To have a full understanding of the buffer effect, we tested a few other common inorganic anions (20–60 mM concentration). In this case, TiO_2 NPs were incubated in buffers containing designated anions and then FAM- A_{15} was added (Figure 5C). Phosphate and citrate strongly inhibited DNA adsorption, where the fluorescence quenching was less than 10% in 2 h. Therefore, these anions are likely to cap the nanoparticle surface. On the other hand, nitrate, sulfate, and acetate have no inhibition effect. It is interesting that citrate is a strong inhibitor, while acetate is not. It is likely that the three carboxyl groups in citrate have a strong chelation effect, which is not present in acetate.

Comparison of ssDNA and dsDNA. In combination with fluorescence quenching and DNA adsorption property, we aim to test whether TiO_2 NPs can be used for DNA detection. To achieve this, there should be a difference between ssDNA and dsDNA. We used a FAM-labeled DNA as a probe and hybridized it with various concentrations of cDNA (i.e., the target DNA) to form dsDNA. The background fluorescence of the hybridized samples was monitored for 5 min before TiO_2 NPs were added (Figure 6A). A higher concentration of the cDNA resulted in a stronger final fluorescence. Even 1 nM cDNA gave a response different from the background, suggesting that high sensitivity might be achieved for this assay method. As a control, the suppression of fluorescence was much less effective if a non-target DNA was used (Figure 6B). Because DNA adsorption takes place mainly via the phosphate group and the phosphate backbone is fully exposed in dsDNA, it is quite surprising that dsDNA showed less fluorescence quenching. This might be explained by the fact that ssDNA is much more flexible and the DNA wraps around TiO_2 to bring the fluorophore to the particle surface. In a rigid dsDNA, however, it is more difficult to effectively bend the DNA and some fluorophores might not be effectively quenched. Note in this case that adsorption was performed at neutral pH, instead of low pH.

CONCLUSION

In summary, we have provided a comprehensive study on TiO_2 NP adsorption of fluorescently labeled DNA oligonucleotides. Care needs to be taken on the surface charge property of TiO_2 NPs, which is strongly affected by the adsorption of simple inorganic anions; phosphate and citrate cap the surface, making TiO_2 NPs negatively charged, even at pH 2. DNA adsorption is

achieved mainly via the backbone phosphate, while the role of the bases is less important. This is supported by the lack of displacement in the presence of free nucleosides, and PNA cannot be adsorbed by TiO_2 NPs. Adsorbed DNA can be displaced by free phosphate. At the same time, pre-adsorption of phosphate and citrate inhibits DNA adsorption, while nitrate, acetate, and chloride have no effect. Both high ionic strength and low pH promote DNA adsorption, and the capacity is drastically increased at pH 2, which is attributed to the DNA base protonation because poly(thymine) DNA is less affected. Note that thymine cannot be protonated at pH 2, while the other three bases can be protonated at pH 2. TiO_2 NP is a strong fluorescence quencher, quenching adsorbed FAM and Cy3 fluorophores. Fluorescence quenching for dsDNA is much less compared to that for ssDNA, which allows for sequence-specific detection of DNA.

ASSOCIATED CONTENT

Supporting Information

DLS (Figure S1) and DNA-length-dependent desorption (Figure S2). This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

*E-mail: liujw@uwaterloo.ca.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

Funding for this work is from the University of Waterloo, the Canadian Foundation for Innovation, the Natural Sciences and Engineering Research Council (NSERC) of Canada, the Canadian Institutes of Health Research (CIHR), and the Early Researcher Award from the Ontario Ministry of Research and Innovation.

REFERENCES

- (1) Adams, L. K.; Lyon, D. Y.; Alvarez, P. J. J. Comparative ecotoxicity of nanoscale TiO_2 , SiO_2 , and ZnO water suspensions. *Water Res.* **2006**, *40*, 3527–3532.
- (2) Jeng, H. A.; Swanson, J. Toxicity of metal oxide nanoparticles in mammalian cells. *J. Environ. Sci. Health, Part A: Toxic/Hazard. Subst. Environ. Eng.* **2006**, *41*, 2699–2711.
- (3) Newman, M. D.; Stotland, M.; Ellis, J. I. The safety of nanosized particles in titanium dioxide- and zinc oxide-based sunscreens. *J. Am. Acad. Dermatol.* **2009**, *61*, 685–692.

- (4) Mikkelsen, L.; Sheykhzade, M.; Jensen, K.; Saber, A.; Jacobsen, N.; Vogel, U.; Wallin, H.; Loft, S.; Moller, P. Modest effect on plaque progression and vasodilatory function in atherosclerosis-prone mice exposed to nanosized TiO₂. *Part. Fibre Toxicol.* **2011**, *8*, 32.
- (5) Song, Y.-Y.; Schmidt-Stein, F.; Bauer, S.; Schmuki, P. Amphiphilic TiO₂ nanotube arrays: An actively controllable drug delivery system. *J. Am. Chem. Soc.* **2009**, *131*, 4230–4232.
- (6) Lachheb, H.; Puzenat, E.; Houas, A.; Ksibi, M.; Elaloui, E.; Guillard, C.; Herrmann, J.-M. Photocatalytic degradation of various types of dyes (Alizarin S, Crocein Orange G, Methyl Red, Congo Red, Methylene Blue) in water by UV-irradiated titania. *Appl. Catal., B* **2002**, *39*, 75–90.
- (7) Ye, L.; Pelton, R.; Brook, M. A.; Filipe, C. D. M.; Wang, H. F.; Brovko, L.; Griffiths, M. Targeted disinfection of *E. coli* via bioconjugation to photoreactive TiO₂. *Bioconjugate Chem.* **2013**, *24*, 448–455.
- (8) Wang, H.; Yang, R. H.; Yang, L.; Tan, W. H. Nucleic acid conjugated nanomaterials for enhanced molecular recognition. *ACS Nano* **2009**, *3*, 2451–2460.
- (9) Giljohann, D. A.; Seferos, D. S.; Daniel, W. L.; Massich, M. D.; Patel, P. C.; Mirkin, C. A. Gold nanoparticles for biology and medicine. *Angew. Chem., Int. Ed.* **2010**, *49*, 3280–3294.
- (10) Saha, K.; Agasti, S. S.; Kim, C.; Li, X.; Rotello, V. M. Gold nanoparticles in chemical and biological sensing. *Chem. Rev.* **2012**, *2739*–2779.
- (11) Zhao, W.; Brook, M. A.; Li, Y. Design of gold nanoparticle-based colorimetric biosensing assays. *ChemBioChem* **2008**, *9*, 2363–2371.
- (12) Liu, J.; Cao, Z.; Lu, Y. Functional nucleic acid sensors. *Chem. Rev.* **2009**, *109*, 1948–1998.
- (13) Li, D.; Song, S. P.; Fan, C. H. Target-responsive structural switching for nucleic acid-based sensors. *Acc. Chem. Res.* **2010**, *43*, 631–641.
- (14) Xu, J.; Zhao, Y. M.; Chen, C. M.; Sun, Y.; Liu, G. Y.; Yan, M. M.; Jiang, Z. Y. Oriented photo-killing tumor using antibody–nano-TiO₂ conjugates and electroporation methods. *Acta Chim. Sin.* **2006**, *64*, 2296–2300.
- (15) Xu, J.; Sun, Y.; Huang, J. J.; Chen, C. M.; Liu, G. Y.; Jiang, Y.; Zhao, Y. M.; Jiang, Z. Y. Photokilling cancer cells using highly cell-specific antibody–TiO₂ bioconjugates and electroporation. *Bioelectrochemistry* **2007**, *71*, 217–222.
- (16) Ye, L.; Pelton, R.; Brook, M. A. Biotinylation of TiO₂ nanoparticles and their conjugation with streptavidin. *Langmuir* **2007**, *23*, 5630–5637.
- (17) Ye, L.; Filipe, C. D. M.; Kavoosi, M.; Haynes, C. A.; Pelton, R.; Brook, M. A. Immobilization of TiO₂ nanoparticles onto paper modification through bioconjugation. *J. Mater. Chem.* **2009**, *19*, 2189–2198.
- (18) Levina, A.; Ismagilov, Z.; Repkova, M.; Shatskaya, N.; Shikina, N.; Tusikov, F.; Zarytova, V. Nanocomposites consisting of titanium dioxide nanoparticles and oligonucleotides. *J. Nanosci. Nanotechnol.* **2012**, *12*, 1812–1820.
- (19) Levina, A. S.; Repkova, M. N.; Ismagilov, Z. R.; Shikina, N. V.; Malygin, E. G.; Mazurkova, N. A.; Zinov'ev, V. V.; Evdokimov, A. A.; Baiborodin, S. I.; Zarytova, V. F. High-performance method for specific effect on nucleic acids in cells using TiO₂~DNA nanocomposites. *Sci. Rep.* **2012**, *2*, 756.
- (20) Zhu, R.-R.; Wang, S.-L.; Zhang, R.; Sun, X.-Y.; Yao, S.-D. A novel toxicological evaluation of TiO₂ nanoparticles on DNA structure. *Chin. J. Chem.* **2007**, *25*, 958–961.
- (21) Suzuki, H.; Amano, T.; Toyooka, T.; Ibuki, Y. Preparation of DNA-adsorbed TiO₂ particles with high performance for purification of chemical pollutants. *Environ. Sci. Technol.* **2008**, *42*, 8076–8082.
- (22) Toyooka, T.; Amano, T.; Suzuki, H.; Ibuki, Y. DNA can sediment TiO₂ particles and decrease the uptake potential by mammalian cells. *Sci. Total Environ.* **2009**, *407*, 2143–2150.
- (23) Amano, T.; Toyooka, T.; Ibuki, Y. Preparation of DNA-adsorbed TiO₂ particles—Augmentation of performance for environmental purification by increasing DNA adsorption by external pH regulation. *Sci. Total Environ.* **2010**, *408*, 480–485.
- (24) Cleaves, H. J.; Jonsson, C. M.; Jonsson, C. L.; Sverjensky, D. A.; Hazen, R. M. Adsorption of nucleic acid components on rutile (TiO₂) surfaces. *Astrobiology* **2010**, *10*, 311–323.
- (25) Rosi, N. L.; Mirkin, C. A. Nanostructures in bionanotechnology. *Chem. Rev.* **2005**, *105*, 1547–1562.
- (26) Zhang, X.; Liu, B.; Dave, N.; Servos, M. R.; Liu, J. Instantaneous attachment of an ultrahigh density of nonthiolated DNA to gold nanoparticles and its applications. *Langmuir* **2012**, *28*, 17053–17060.
- (27) Zhang, X.; Servos, M. R.; Liu, J. Surface science of DNA adsorption onto citrate-capped gold nanoparticles. *Langmuir* **2012**, *28*, 3896–3902.
- (28) Wu, M.; Kempaiah, R.; Huang, P.-J. J.; Maheshwari, V.; Liu, J. Adsorption and desorption of DNA on graphene oxide studied by fluorescently labeled oligonucleotides. *Langmuir* **2011**, *27*, 2731–2738.
- (29) Wang, F.; Liu, B.; Huang, P.-J. J.; Liu, J. Rationally designed nucleobase and nucleotide coordinated nanoparticles for selective DNA adsorption and detection. *Anal. Chem.* **2013**, *85*, 12144–12151.
- (30) Pautler, R.; Kelly, E. Y.; Huang, P.-J. J.; Cao, J.; Liu, B.; Liu, J. Attaching DNA to nanoceria: Regulating oxidase activity and fluorescence quenching. *ACS Appl. Mater. Interfaces* **2013**, *5*, 6820–6825.
- (31) Liao, D. L.; Wu, G. S.; Liao, B. Q. Zeta potential of shape-controlled TiO₂ nanoparticles with surfactants. *Colloids Surf., A* **2009**, *348*, 270–275.
- (32) Xu, G.; Zhang, J.; Li, G.; Song, G. Effect of complexation on the zeta potential of titanium dioxide dispersions. *J. Dispersion Sci. Technol.* **2003**, *24*, 527–535.
- (33) Nelson, B. P.; Candal, R.; Corn, R. M.; Anderson, M. A. Control of surface and ζ potentials on nanoporous TiO₂ films by potential-determining and specifically adsorbed ions. *Langmuir* **2000**, *16*, 6094–6101.
- (34) Yang, R. H.; Jin, J. Y.; Chen, Y.; Shao, N.; Kang, H. Z.; Xiao, Z.; Tang, Z. W.; Wu, Y. R.; Zhu, Z.; Tan, W. H. Carbon nanotube-quenched fluorescent oligonucleotides: Probes that fluoresce upon hybridization. *J. Am. Chem. Soc.* **2008**, *130*, 8351–8358.
- (35) Lu, C. H.; Yang, H. H.; Zhu, C. L.; Chen, X.; Chen, G. N. A graphene platform for sensing biomolecules. *Angew. Chem., Int. Ed.* **2009**, *48*, 4785–4787.
- (36) Huang, P.-J. J.; Liu, J. DNA-length-dependent fluorescence signaling on graphene oxide surface. *Small* **2012**, *8*, 977–983.
- (37) Dubertret, B.; Calame, M.; Libchaber, A. J. Single-mismatch detection using gold-quenched fluorescent oligonucleotides. *Nat. Biotechnol.* **2001**, *19*, 365–370.
- (38) Lu, W. B.; Qin, X. Y.; Luo, Y. L.; Chang, G. H.; Sun, X. P. CdS quantum dots as a fluorescent sensing platform for nucleic acid detection. *Microchim. Acta* **2011**, *175*, 355–359.
- (39) Hill, H. D.; Millstone, J. E.; Banholzer, M. J.; Mirkin, C. A. The role radius of curvature plays in thiolated oligonucleotide loading on gold nanoparticles. *ACS Nano* **2009**, *3*, 418–424.
- (40) Zhang, X.; Liu, B.; Servos, M. R.; Liu, J. Polarity control for nonthiolated DNA adsorption onto gold nanoparticles. *Langmuir* **2013**, *29*, 6091–6098.
- (41) Zhang, X.; Servos, M. R.; Liu, J. Instantaneous and quantitative functionalization of gold nanoparticles with thiolated DNA using a pH-assisted and surfactant-free route. *J. Am. Chem. Soc.* **2012**, *134*, 7266–7269.
- (42) Huang, P.-J. J.; Kempaiah, R.; Liu, J. Synergistic pH effect for reversible shuttling aptamer-based biosensors between graphene oxide and target molecules. *J. Mater. Chem.* **2011**, *21*, 8991–8993.