



Nanoscale

Accepted Manuscript

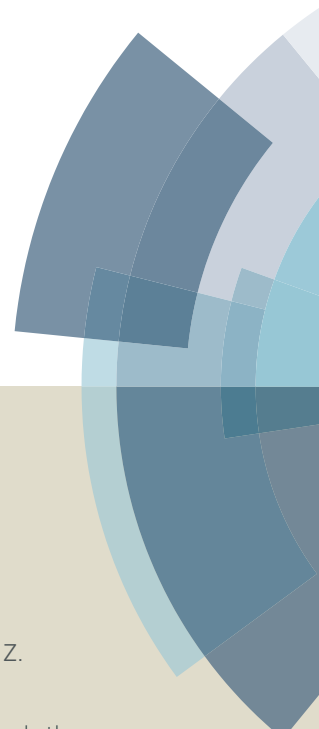

This article can be cited before page numbers have been issued, to do this please use: S. Liu, N. Zhao, Z. Cheng and H. Liu, *Nanoscale*, 2015, DOI: 10.1039/C5NR00070J.

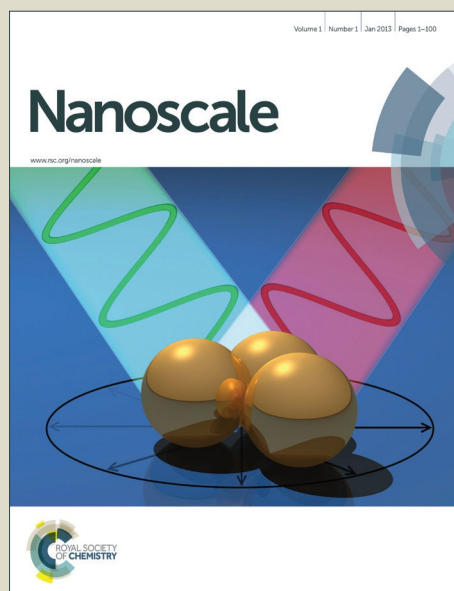

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Amino-functionalized Green Fluorescent Carbon Dots as Surface Energy Transfer Biosensors for Hyaluronidase

Siyu Liu^a, Ning Zhao^a, Zhen Cheng^{*b} and Hongguang Liu^{*a}

Amino-functionalized fluorescent carbon dots have been prepared by hydrothermal treatment of glucosamine with excess pyrophosphate. The produced carbon dots showed stabilized green emission fluorescence at various excitations wavelength and pH environments. Herein, we demonstrate the surface energy transfer between the amino-functionalized carbon dots and negatively charged hyaluronate stabilized gold nanoparticles. Hyaluronidase can degrade hyaluronate and break down the hyaluronate stabilized gold nanoparticles to inhibit the surface energy transfer. The developed fluorescent carbon dots/gold nanoparticles system can be utilized as a biosensor for sensitive and selective detection of hyaluronidase with two modes including fluorescence measurement and colorimetric analysis.

Introduction

Fluorescent nanomaterials have attracted considerable attention in biomedical fields including bioimaging, drug delivery and biosensing because of their small size, long fluorescence lifetime, tunable fluorescence emission and high photostability.¹⁻² In the development of fluorescent nanomaterials, studies on the applications of quantum dots (QDs) hold important positions.³ However, the leakage of heavy metal elements such as cadmium, lead, mercury and silver resulting in cytotoxicity and environmental pollution severely hampers QDs' application.⁴ Recently, fluorescent carbon dots (CDs) have been proposed as a class of promising and less toxic nanomaterials to replace traditional QDs.⁵

Since Sun and co-workers first reported nanoscale bright photoluminescence carbon nanoparticles upon simple surface passivation,⁶ fluorescent CDs have shown attractive properties for the use in bioimaging and biosensing due to their high photostability, excellent cell membrane permeability, water solubility and biocompatibility.⁷ So far, a series of synthesis methods for fluorescent CDs have been developed. One approach is to produce from larger carbon sources through laser irradiation, electrochemical and chemical oxidation of graphite, carbon nanotubes or soots of candles.⁸ The other approach is to synthesize from carbon precursors such as glycerol, glycol, glucose, sucrose, citric acid, etc. through chemical and hydrothermal oxidation or microwave pyrolysis.⁹ However, most of these methods usually need complex procedures or modifications to improve the surface state of the CDs. The amino-group functionalization could effectively increase the biocompatibility and hydrophilicity of CDs and make it easy for further modifications.^{10a} But the surface modification using amine-terminated compounds are complex and time-consuming.^{10b} Yang et al. proposed a method to prepare amino-functionalized fluorescent CDs by hydrothermal carbonization of chitosan,^{10c} but the poor water solubility of chitosan and highly

acidic synthetic environments restricted its broad applications. Herein, we report a one-pot synthetic route to prepare water-soluble amino-functionalized CDs through hydrothermal treatment of glucosamine in excess pyrophosphates solution, and we further use it for imaging biomarkers such as hyaluronidases (Hase).

Hase is an extracellular matrix digesting endoglycosidases and can degrade hyaluronate (HA), which is a highly negatively charged linear mucopolysaccharide.¹¹ Hase is involved in a variety of physiological and pathological processes including fertilization, embryogenesis, maintenance of the elastoviscosity in tissues, wound healing, inflammation, and tumor growth.¹² In recent years, the changes of Hase level in human blood and urine have been found to be associated with the growth of numerous human tumors, such as bladder cancers and prostate cancers.¹³ Therefore, to develop a highly sensitive and specific technique for the detection of Hase level is important and desired. Until now, series of fluorescent labeled substrates including HA have been designed for sensitive and real-time monitoring of Hase level.^{14, 15} For instance, Chib et al. used a HA probe labeled with fluorescein as a donor and rhodamine as an acceptor to monitor the digestion of HA probe with different concentrations of Hase in synthetic urine via fluorescence emission.^{15a} Fluorescent CDs, as novel fluorescent nanosensors, have been utilized to detect a variety of biological molecules and stimuli such as Hg²⁺, Pb²⁺, Ag⁺, DNA, glucose, tissue pH based on fluorescence changes.^{16, 17} However, the reports on fluorescent CDs-based nanosensors for enzyme assay are very rare.

Gold nanoparticles (Au NPs), as a kind of nanomaterial, possess strong light scattering, absorption ability, and large surface-to-volume ratio. And the surface of Au NP follows the expression given by surface energy transfer (SET) that allows a 22 nm detection length scale instead of 10 nm detection length in fluorescence resonance energy transfer.¹⁸ Because of the highly sensitive fluorescence quenching ability of Au NPs, the novel SET process possesses great potential for target detection and

molecular interaction studies.^{18c} In this work, we first designed a facile SET system between the positively charged amino-functionalized carbon dots and negatively charged hyaluronate stabilized gold nanoparticles (HA-Au NPs) for the detection of Hase based on its ability to degrade HA. Moreover, the Hase level changes can be monitored simultaneously by the fluorescence emission intensity and visible light absorption value of the CDs/HA-Au NPs SET assay system.

Experimental section

Apparatus

The fluorescence spectra were measured with a Thermo Scientific Lumina fluorescence spectrometer with a xenon lamp using right-angle geometry. UV-Vis absorption spectra were obtained by using a Biotek SynergyTM H1 microplate reader. FT-IR spectra were recorded with a Bruker IFS66V FT-IR spectrometer equipped with a DGTS detector (32 scans). Transmission electron microscopy (TEM) experiments were performed on a Philips Tecnai F20 TEM operating at 200KV acceleration voltage. TEM samples were prepared by dropping the aqueous fluorescent CDs or HA-Au NPs solution onto carbon-coated copper grids and allowing the excess solvent to evaporate.

Chemicals and materials

All reagents were of at least analytical grade. The water used in all experiments had a resistivity higher than 18 MΩ cm⁻¹. Potassium phosphate (K₃PO₄), sodium phosphate (Na₃PO₄), sodium hydrogen phosphate (Na₂HPO₄), sodium dihydrogen phosphate (NaH₂PO₄), sodium pyrophosphate (Na₄P₂O₇), sodium triphosphate (Na₅P₃O₁₀), sodium hexametaphosphate (Na₆P₆O₁₈) were purchased from Sinopharm Chemical Reagent Co., Ltd. D-glucosamine hydrochloride, sodium borohydride (NaBH₄) chloroauric acid (HAuCl₄), sodium hyaluronate, Hase (400 U/mg), fetal bovin serum and cellulose membrane dialysis tubing (3KDa) were purchased from Sigma-Aldrich Corporation.

Synthesis of amino-functionalized fluorescent CDs

In a typical synthetic route, amino-functionalized fluorescent CDs were prepared as following: 1 mL of 75 mmol/L D-glucosamine hydrochloride solution was added into a 14 mL of deionized water solution containing 0.938 mmol sodium pyrophosphate with vigorous stirring at room temperature. After 10 minutes, the solution was transferred into a teflon lined stainless steel autoclave with a volume of 25 mL. The autoclave was maintained at 180 °C for 10 h and then cooled down to room temperature by a natural cooling process. The obtained yellow-brown CDs solution was centrifuged with a speed of 12,000 rpm at 4 °C for 40 min to remove the less deposit and excess sodium pyrophosphate. The upper yellow-brown solution was dialyzed in membrane tubing with a molecular weight cut-off of 3 KDa against ultrapure water to remove small molecules and ions and then stored at 4 °C. The purified CDs solution were freeze-dried into powder, and the concentration of amino-functionalized fluorescent CDs in solution was about 2.1 mg/mL as measured by the dry weight analysis method.

Synthesis of HA-Au NPs

The HA-Au NPs were synthesized according to the previous

reports with some modifications.^{18d,19} In a typical synthetic process, HA-Au NPs were prepared as follows: 1 mL of HAuCl₄ (0.12 mol/L) solution was added into 50 mL 0.01 % (W/V) sodium hyaluronate aqueous solution with vigorous stirring for 20 minutes at room temperature. After that, 1 mL of NaBH₄ (4 mg/mL) was slowly injected into above solution, and solution color changed from yellow to red purple indicating the formation of amounts of HA-Au NPs. The reaction mixture was allowed to proceed for another 5 minutes under vigorous stirring. After that the product was purified to remove small molecule and ions via ultra-filtration (10 KDa ultra-filtration centrifuge tube) and dissolved in deionized water again. The purified HA-Au NPs solution was stored at 4 °C.

The SET system for the detection of Hase

The Hase detection process was carried out as follows. 20 μL 0.1 mol/L NaH₂PO₄-Na₂HPO₄ buffer solution (pH 6.0), 20 μL CDs solution (0.21 mg/mL), 20 μL HA-Au NPs and different concentration of Hase were respectively added into 200 μL calibrated centrifuge tube. Then the solution was diluted to 200 μL with deionized water followed by the incubation at 37 °C for 2 hours. The fluorescence emission and UV-Vis absorption spectra were recorded and used for quantitative analysis.

Quantum yield measurements

The quantum yield (QY) of CDs was determined by comparing with reference fluorophore. Fluorescein (QY_R = 0.79) was used as reference fluorophore for the determination of QY. For a standard measurement, the fluorescein was dissolved in 0.1 mol/L NaOH (refractive index n = 1.33), and CDs were dispersed in deionized water (n = 1.33). Then the quantum yield was calculated by the following equation:

$$QY = QY_R \times (I/I_R) \times (A_R/A) \times (n^2/n_R^2)$$

I is the integrated fluorescence emission intensity, A is the absorbance intensity and n is the refractive index. The subscript R refers to the reference fluorophore of known quantum yield.


Results and discussion

The preparation and characterizations of amino-functionalized CDs

In the present work, we proposed a one-pot green route to prepare green-emitting amino-functionalized CDs and then adopted the synthesized CDs as a new type of selective and sensitive biosensor for detection of Hase based on a SET system (Scheme 1). As shown in Scheme 1A which displayed a typical CDs synthesis, pyrophosphate and glucosamine that is an important nutrient in human chondrocytes were dissolved in aqueous solution at room temperature. When the reaction mixture was heated from room temperature to 180 °C, the colorless transparent reaction solution turned into yellow brown and produced highly green fluorescent product under an ultraviolet light. In the synthetic process, glucosamine was adopted as a natural nitrogen-doped carbon source, and sodium pyrophosphate was used as a catalytic agent.⁹

In previous reports, nitric acid, chlorosulfonic acid or phosphoric acid, etc were utilized as the oxidizing agent or

catalytic agent during synthesis of CDs.^{8,9} Here, we firstly reported the use of sodium pyrophosphate for the preparation of CDs. Fig.1 showed the fluorescence emission spectra of amino-functionalized CDs

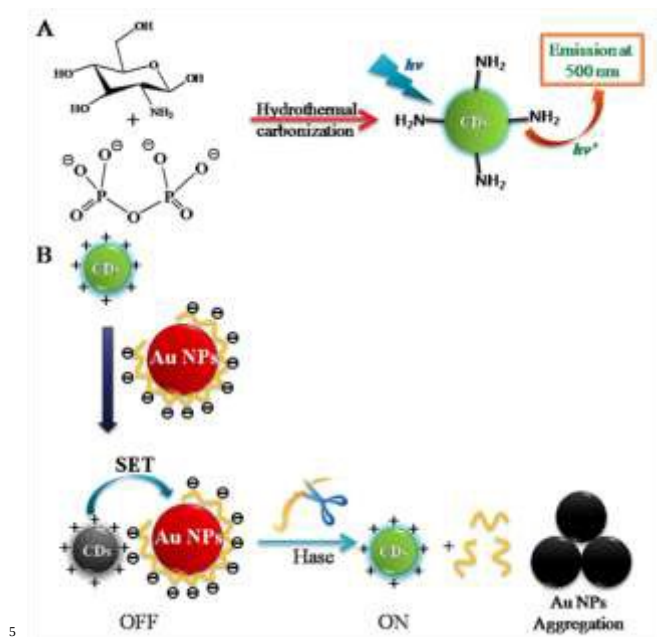

Scheme 1 (A) The schematic illustration of the synthetic process of amino-functionalized CDs and (B) the use of prepared CDs and Au NPs as a SET biosensor system for Hase.

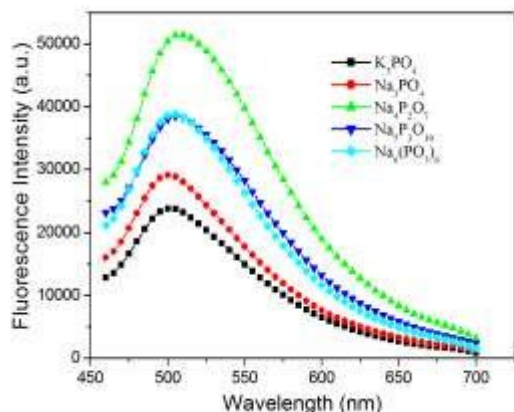


Fig.1 Fluorescence emission spectra of CDs excited at 420 nm respectively prepared with potassium phosphate (125 mmol/L), sodium phosphate (125 mmol/L), sodium pyrophosphate (62.5 mmol/L), sodium triphosphate (41.7 mmol/L) or sodium hexametaphosphate (20.8 mmol/L).

respectively prepared with potassium phosphate, sodium phosphate, sodium pyrophosphate, sodium triphosphate, sodium hexametaphosphate. It is indicated that the polyphosphates showed a better results for inducing highly fluorescent CDs than monophosphate, and highly fluorescent emission peak around 500 nm belonging to CDs was observed with excess sodium pyrophosphate as the catalytic agent. Moreover, Fig.2 offered the fluorescence changes of the prepared

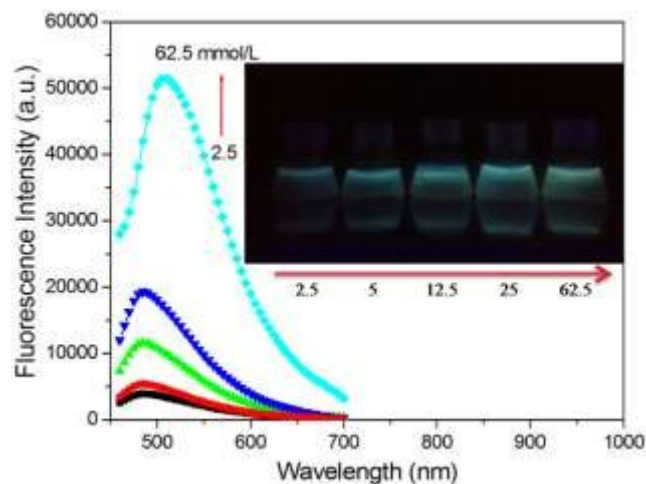


Fig.2 Fluorescence emission spectra of CDs synthesized by different concentrations of sodium pyrophosphate increasing from 2.5 to 62.5 mmol/L (2.5, 5, 12.5, 25, 62.5 mmol/L). The inset picture shows the color change of the CDs solutions synthesized with different concentration of sodium pyrophosphate under a UV beam of 365 nm.

CDs solution with different concentration of sodium pyrophosphate. When the pyrophosphate concentration just reached 2.5 mmol/L, the synthesized CDs solution showed very weak green emission fluorescence signal and there were some black deposits at the bottom of original CDs solution. With the pyrophosphate concentration increasing from 2.5 to 62.5 mmol/L, the fluorescence intensity of CDs enhanced significantly also with an increase of QYs from 0.5 to 16.8%. At the 62.5 mmol/L pyrophosphate concentration, the prepared CDs solution offered maximum fluorescence emission and QY (16.8%). And a red-shift of fluorescence emission wavelength (from 480 to 500 nm) with the increase of pyrophosphate concentration was also observed which corresponded to the size growth of fluorescent CDs.^{20a} At the same time, with the increase of pyrophosphate concentration, the black deposit at the bottom of original CDs solution significantly reduced, that further indicated pyrophosphate effectively prevented carbon nuclei from growing and assembling into large carbon particles during the hydrothermal carbonization.²⁰ The changing trends of UV-Vis absorption spectra attributed to CDs solution with progressively increased pyrophosphate concentration were also consistent with their fluorescence spectra (Fig.S1A, ESI†). Furthermore, the enhanced fluorescence emission signal of CDs solution with increasing pyrophosphate concentration could be directly observed by the naked-eye under a UV beam of 365 nm (Fig.2inset). It is generally known that the fluorescence emission of CDs arises from the radiative recombination of the excitons trapped by the surface defects that are produced in the passivated procedure.^{10c} So far, most of the prepared fluorescent CDs show a similar phenomenon which is their emission spectra is highly dependent on the excitation wavelengths.^{8, 9, 10} And these prepared CDs usually exhibit blue photoluminescence under ultraviolet light excitation. However, as shown in Fig.2inset, the prepared CDs solution emitted bright green fluorescence under ultraviolet light. Furthermore, Fig.S1B (ESI†) revealed that with excitation wavelengths increase from 380 to 440 nm, the green fluorescence emission peak position of CDs solution could be almost constant.

The fluorescence emission changes of CDs fabricated at different temperatures were also recorded (Fig.S2, ESI[†]). It was noted that CDs solution prepared at 180 °C had the optimal fluorescence emission signal. And the morphology and size of CDs synthesized by the hydrothermal treatment of glucosamine and excess pyrophosphate were observed by TEM (Fig. S3A, ESI[†]). It could be found that the generated CDs were near spherical with well-dispersion and the sizes distribution gave an average size of 4.11 nm with ± 1.23 nm. The FT-IR spectra were utilized to further confirm the chemical structure of the synthesized CDs. The broad O–H stretching vibration and absorption (3390 cm^{-1} , 1000 cm^{-1}), the stretching mode of C=O (1710 cm^{-1}), a pair of asymmetric and symmetric stretching modes of C–O–C (1340 cm^{-1} , 1180 cm^{-1}), the asymmetric stretching and deformational vibration of –NH_2 (3390 and 1660 cm^{-1}) and the absorption band of C–N (1300 cm^{-1}) were all observed in the FT-IR spectra of the CDs (Fig.S3B, ESI[†]). And the presence of –NH_2 and C–N further indicated that the abundant –NH_2 group could remain at the surface of CDs even after the hydrothermal carbonization. Besides, the C=C stretching vibration in the CDs was found by the absorption band around 1590 cm^{-1} , 1510 cm^{-1} and 1380 cm^{-1} which indicated the surface of CDs was partially carbonized during the hydrothermal process.²¹ Therefore, the obtained CDs were natural amino-functionalized green fluorescent CDs.

To further explore the potential application of amino-functionalized CDs in biosensing, one of the primary requirements is water-solubility and stability under various pH and ionic environments. While CDs with abundant hydroxyl and amino groups were inherently water-soluble, their stability in various environments was further tested in Fig.S4 and Fig.S5 (ESI[†]). Fig.S4 indicated the fluorescence intensity of the pre-prepared CDs solution was almost the same in different pH environments, although a slight decrease was observed for the CDs with the pH of environment over 6.4. That is very different from many other water-soluble fluorescence dyes and quantum dots which usually offer obvious decrease fluorescence emission with the decrease of pH value and poor fluorescence and stability in acid environment.²² Moreover, some traditional dyes and quantum dots are faced with the interference of some ions and molecules such as Zn^{2+} , Fe^{3+} and L-cysteine (Cys).²³ As shown in Fig.S5, we investigated the effect of various ions and molecules including K^+ , Na^+ , Ca^{2+} , Mg^{2+} , Zn^{2+} , Ni^{2+} , Fe^{3+} , Cu^{2+} , glucose (Glu), glycine (Gly), histidine (His), Cys on the fluorescence of CDs. It was found that the CDs were also highly stable under various ions and molecules environment. The high stability of CDs provided a significant merit in sensing applications.

The SET system between CDs and HA-Au NPs

As shown in Fig.S6A (ESI[†]), the zeta potentials of amino-functionalized CDs and HA-Au NPs solution were determined to be $+12.8$ and -2.9 mV respectively. Therefore, the amino-functionalized CDs with positive charge generated from protonated amine groups could attract HA-Au NPs with negatively charged by electrostatic interactions.²⁴ And the TEM image further showed some amino-functionalized CDs were distributed nearby HA-Au NPs in the mixture solution composed of CDs and HA-Au NPs (Fig.S6B, ESI[†]). It is well known that Au NPs

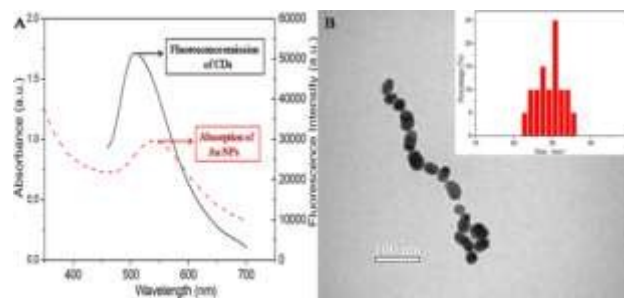


Fig.3 (A) The fluorescence emission spectra of CDs (solid line) and UV-Vis absorption spectra of HA-Au NPs solution (dashed line). (B) The TEM image of HA-Au NPs.

exhibited efficient ability of fluorescence quenching due to the non-radioactive electronic excitation energy transfer from the fluorescent probe to Au NPs.²⁵ The HA-Au NPs were prepared via the NaBH_4 -reduction route, which offered the maximum absorption peak around 534 nm with a near spherical shape and a size centered at 22–27 nm (Fig.3). It can be seen that from Fig.3A, there was a large overlap between the fluorescence emission spectra of prepared amino-functionalized CDs and absorption spectra of HA-Au NPs. Therefore, we designed an efficient SET system between CDs and HA-Au NPs, and there was an obvious fluorescence quenching of CDs with the addition of HA-Au NPs (Fig.S7, ESI[†]). Moreover, the fluorescence lifetime of amino-functionalized CDs was determined to be 2.7 ns, and the SET system composed of CDs and HA-Au NPs was 2.3 ns (Fig.S8, ESI[†]). With the addition of HA-Au NPs, the shorter lifetime from the SET system could help rule out the possibility of static quenching.

The SET system for detection of Hase

Hase, as a digesting endoglycosidases, can specially degrade linear HA molecules. And we designed a detection strategy for Hase that was illustrated in Scheme 1B. HA molecules on the surface of Au NPs can effectively protect Au NPs and prevent aggregation. In the presence of enough Hase, HA molecules would be decomposed into low molecular weights fragments that lead to the aggregation of Au NPs and the exit from the SET system. Fig.S9A (ESI[†]) displayed the fluorescence signal changes of CDs/HA-Au NPs SET system with the addition of increasing Hase concentration (0–100 U/mL) incubated for different time (0–120 minutes). The fluorescence intensity increased gradually until the reaction time reached 120 minutes. Therefore 120 minutes of incubation time was used in the further Hase assay. The color changes of CDs/HA-Au NPs SET system response to 100 U/mL Hase were provided in Fig.S9B. Incubated with Hase for 2 hours, the CDs/HA-Au NPs solution changed from purple red into light red. Not only that, some black deposits could be observed at the bottom of CDs/HA-Au NPs incubated with Hase solution after low speed centrifugation, which visually indicated the generation of Au NPs aggregation with enough Hase.

As shown in Fig.4, the quenched fluorescence of CDs induced by HA-Au NPs was gradually recovered with the increase of Hase concentration that was caused by the aggregation of Au NPs and its exit from the SET system. And Fig.4inset demonstrated that there was a good linear relationship between the relative fluorescence F/F_0 (F_0 is the original

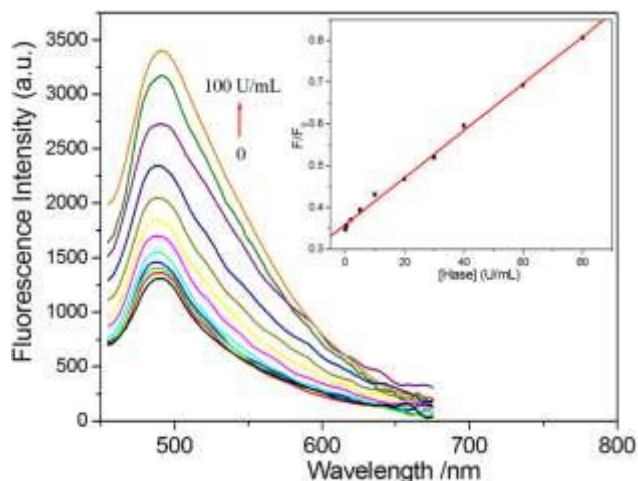


Fig.4 Fluorescence spectra of CDs/HA-Au NPs SET system incubated with different concentration of Hase (0, 0.1, 0.5, 2, 5, 10, 20, 30, 40, 60, 80, 100 U/mL) for 2 hours. Inset shows the linear plots of F/F_0 versus the Hase concentration in the range of 0.1-80 U/mL. Reaction condition: 10 mmol/L $\text{NaH}_2\text{PO}_4\text{-Na}_2\text{HPO}_4$ buffer solution (pH 6.0) at 37 °C.

fluorescence intensity of CDs, and F is the fluorescence intensity of CDs/HA-Au NPs with the addition of various concentration of Hase) and Hase concentrations in the concentration range from 0.1 to 80 U/mL. The regression equation could be described as following:

$$F/F_0 = 0.3593 + 0.0056[\text{Hase}], \text{ U/mL} \quad (1)$$

The corresponding regression coefficient (R^2) is 0.998, and the detection limit for Hase was 0.06 U/mL calculated following the 3σ IUPAC criteria. As shown in Fig.S10, Hase and a series of proteins including bovine serum albumin (BSA), human serum albumin (HSA), bovine hemoglobin (HB), lysozyme (Lyz), trypsin (Try), glutathione (GSH) was respectively added into the CDs/HA-Au NPs assay system to incubate for 120 minutes, and only the Hase was able to effectively induce the fluorescence recovery of the assay solution due to its specific ability to degrade HA. Our proposed assay system yielded weak fluorescence responses to other proteins that indicated this strategy had a high selectivity toward Hase.

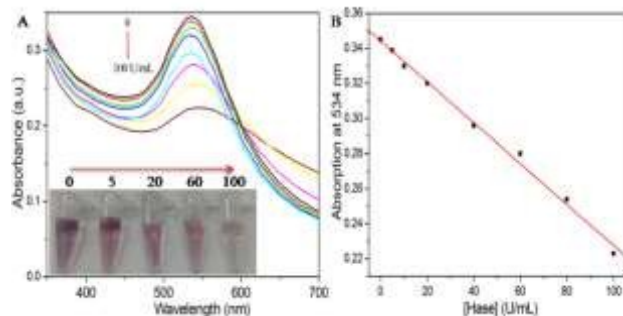


Fig.5 (A) UV-Vis absorption spectra of CDs/HA-Au NPs SET system incubated with different concentrations of Hase (0, 5, 10, 20, 40, 60, 80, 100 U/mL) for 2 hours. The inset picture shows the color change of the SET system solutions incubated with different concentrations of Hase (0, 5, 20, 60, 100 U/mL) for 2 hours. (B) The standard curve of absorbance at 534 nm as the function of Hase concentration (0, 5, 10, 20, 40, 60, 80, 100 U/mL).

100 U/mL). Reaction condition: 10 mmol/L $\text{NaH}_2\text{PO}_4\text{-Na}_2\text{HPO}_4$ buffer solution (pH 6.0) at 37 °C.

In addition, Fig.5A revealed that the absorption peak centered 534 nm of the CDs/HA-Au NPs solutions presented an obvious reduction with the increase of Hase concentration. At the same time, there was also a color gradient from purple red to light red incubated with the increase of Hase concentration in the assay system (Fig.5Ainset). Therefore, this assay offered a simple route for quantitative estimation of Hase. Fig.5B showed a standard curve in which the absorbance at 534 nm (A_{534}) of CDs/HA-Au NPs solutions was plotted as a function of various Hase concentrations. The standard curve could be described as following:

$$A_{534} = 0.3443 - 0.0012[\text{Hase}], \text{ U/mL} \quad (2)$$

The corresponding regression coefficient R^2 was 0.996, and the detection limit for Hase was 1 U/mL with the dynamic range from 0 to 100 U/mL. Therefore, the Hase detection could be also performed with absorbance analysis besides fluorescence measurement.

Serum samples detection

In order to evaluate the feasibility of the proposed method in real samples detection, the developed detection system was applied to the determination of Hase in fetal bovin serum samples. The commercial fetal bovine serum was diluted by 25 times with deionized water and then adjusted to pH 6.0. Different concentrations of Hase were added to the diluted serum samples to prepare the spiked samples. The results obtained by standard addition method were shown in Table S1, and the accuracy of the proposed method was evaluated by determining the recoveries of Hase in real samples. It can be seen that the recoveries in the real samples was between 102-108% and the RSD was not over 4.7%. The above results demonstrated the potential applicability of this method for the detection of Hase in serum samples.

Conclusion

In this study, for the first time, we demonstrated the highly fluorescent amino-functionalized CDs could be prepared by hydrothermal treatment of glucosamine with excess pyrophosphate. The amino-functionalized CDs offered constant green fluorescence emission at various excitation wavelengths and high stability when exposed to different pH and ionic environments. We further developed a facile SET assay system based on the amino-functionalized CDs and HA-Au NPs for the fluorescent detection of Hase. Moreover, the absorbance measurement could be conveniently used for quantitatively analysis of Hase based on the color change of the SET assay solution.

Acknowledgements

This work was supported by the Natural Science Foundation of China (81201141), the Fundamental Research Funds for Central Universities of China (N130520001), and the Liaoning Provincial Educational Commission (L2014095).

Notes and references

- ^a Institute of Molecular Medicine, College of life and health sciences, Northeastern University, Shenyang 110000, China.
E-mail: simonliu@mail.neu.edu.cn
- ^b Molecular Imaging Program at Stanford, Stanford University, Palo Alto, CA 94301, USA. E-mail: zcheng@stanford.edu
- 1 J. K. Jaiswal, H. Mattoussi, J. M. Mauro and S. M. Simon, *Nat. Biotechnol.*, 2003, **21**, 47.
 - 2 X. Michalet, F. F. Pinaud, L. A. Bentolila, J. M. Tsay, S. Doose, J. J. Li, G. Sundaresan, A. M. Wu, S. S. Gambhir and S. Weiss, *Science*, 2005, **307**, 538.
 - 3 C.Q. Ding, A.W. Zhu and Y. Tian, *Accounts. Chem. Res.*, 2014, **47**, 20.
 - 4 a) J. H. Gao and B. Xu, *Nano Today*, 2009, **4**, 37; b) X. Y. Li, H. Q. Wang, Y. Shimizu, A. Pyatenko, K. Kawaguchi and N. Koshizaki, *Chem. Commun.*, 2011, **47**, 932.
 - 5 S. N. Baker and G. A. Baker, *Angew. Chem., Int. Ed.*, 2010, **49**, 6726.
 - 6 Y. P. Sun, B. Zhou, Y. Lin, W. Wang, K. A. S. Fernando, P. Pathak, M. J. Mezziani, B. A. Harruff, X. Wang, H. F. Wang, P. J. G. Luo, H. Yang, M. E. Kose, B. L. Chen, L. M. Veca and S. Y. Xie, *J. Am. Chem. Soc.*, 2006, **128**, 7756.
 - 7 a) L. Y. Zheng, Y. W. Chi, Y. Q. Dong, J. P. Lin and B. B. Wang, *J. Am. Chem. Soc.*, 2009, **131**, 4564; b) S. T. Yang, L. Cao, P. G. Luo, F. S. Lu, X. Wang, H. F. Wang, M. J. Mezziani, Y. F. Liu, G. Qi and Y. P. Sun, *J. Am. Chem. Soc.*, 2009, **131**, 11308; c) Z. A. Qiao, Y. F. Wang, Y. Gao, H. W. Li, Y. L. Liu and Q. S. Huo, *Chem. Commun.*, 2010, **46**, 8812–8814; d) D. Y. Pan, J. C. Zhang, Z. Li and M. H. Wu, *Adv. Mater.*, 2010, **22**, 734.
 - 8 a) S. L. Hu, K. Y. Niu, J. Sun, J. Yang, N. Q. Zhao and X. W. Du, *J. Mater. Chem.*, 2009, **19**, 484; b) L. Y. Zheng, Y. W. Chi, Y. Q. Dong, J. P. Lin and B. B. Wang, *J. Am. Chem. Soc.*, 2009, **131**, 4564; c) V. N. Mochalin and Y. Gogotsi, *J. Am. Chem. Soc.*, 2009, **131**, 4594; d) Z. A. Qiao, Y. F. Wang, Y. Gao, H. W. Li, Y. L. Liu and Q. S. Huo, *Chem. Commun.*, 2010, **46**, 8812.
 - 9 a) S. Chandra, P. Das, S. Bag and D. Laha, *Nanoscale*, 2011, **3**, 1533; b) J. Hou, J. Yan, Q. Zhao, Y. Li, H. Ding and L. Ding, *Nanoscale*, 2013, **5**, 9558; c) D. Y. Pan, J. C. Zhang, Z. Li, Z. W. Zhang, L. G. and M. H. Wu, *J. Mater. Chem.*, 2011, **21**, 3565; d) H. Peng and J. Travas-Sejdic, *Chem. Mater.*, 2009, **21**, 5563.
 - 10 a) C. M. Lee, H. J. Jong, S. L. Kim, E. M. Kim, D. W. Kim, S. T. Lim, K. Y. Jang, Y. Y. Jeon, J. W. Nah, M. H. Sohn, *Int. J. Pharm.*, 2009, **371**, 163; b) Z. A. Qiao, Y. F. Wang, Y. Gao, H. W. Li, T. Y. Dai, Y. L. Liu and Q. S. Huo, *Chem. Commun.*, 2010, **46**, 8812; c) Y. H. Yang, J. H. Cui, M. T. Zheng, C. F. Hu, S. Z. Tan, Y. Xiao, Q. Yang and Y. L. Liu, *Chem. Commun.*, 2012, **48**, 380.
 - 11 a) M. W. Kramer, D. O. Escudero, S. D. Lokeshwar, R. Golshani, O. O. Ekwenna, K. Acosta, A. S. Merseburger, M. Soloway and V. B. Lokeshwar, *Cancer*, 2011, **117**, 1197; b) C. J. Whatcott, H. Y. Han, R. G. Posner and G. Hostetter, D. D. Von-Hoff, *Cancer. Discov.*, 2011, **1**, 291.
 - 12 a) H. F. Xie, F. Zeng, and S. Z. Wu, *Biomacromolecules*, 2014, **15**, 3383; b) V. B. Lokeshwar, V. Estrella, L. Lopez, M. Kramer, P. Gomez, M. S. Soloway, and B. L. Lokeshwar, *Cancer. Res.*, 2006, **66**, 11219; c) J. J. Roberts, R. M. Elder, A. Jayaraman and S. J. Bryant, *Biomacromolecules*, 2014, **15**, 1132.
 - 13 a) S. Eissa, M. Swellam, H. Shehata, I. El-Khouly, T. El-Zayat, and O. El-Ahmady, *J. Urol.*, 2010, **183**, 493; b) V. B. Lokeshwar, D. Rubinowicz, G. L. Chroeder, E. Forgacs, J. D. Minna, N. L. Block, M. Nadji and B. L. Lokeshwar, *J. Biol. Chem.*, 2001, **276**, 11922.
 - 14 a) R. Jin, L. S. M. Teixeira, P. J. Dijkstra, C. A. van Blitterswijk, M. Karperien and J. Feijen, *Biomaterials*, 2010, **31**, 3103; b) S. W. Liao, T. B. Yu and Z. B. Guan, *J. Am. Chem. Soc.*, 2009, **131**, 17638.
 - 15 a) R. Chib, S. Raut, R. Fudala, A. Chang, M. Mummert, R. Rich, Z. Gryczynski, and I. Gryczynski, *Curr. Pharm. Biotechnol.*, 2013, **14**, 470; b) R. Fudala, M. E. Mummert, Z. Gryczynski and Ignacy Gryczynski, *J. Photoch. Photobiol. B.*, 2011, **104**, 473; c) L. S. Zhang, M. E. Mummert, *Anal. Biochem.*, 2008, **379**, 80; d) R. Fudala, M. E. Mummert, Z. Gryczynski, R. Rich, J. L. Borejdo and I. Gryczynski, *J. Photoch. Photobiol. B.*, 2012, **106**, 69.
 - 16 a) S. Liu, J. Q. Tian, L. Wang, Y. W. Zhang, X. Y. Qin, Y. L. Luo, A. M. Asiri, A. O. Al-Youbi, and X. P. Sun, *Adv. Mater.*, 2012, **24**, 2037; b) W. B. Lu, X. Y. Qin, S. Liu, G. H. Chang, Y. W. Zhang, Y. L. Luo, A. M. Asiri, A. O. Al-Youbi, and X. P. Sun, *Anal. Chem.*, 2012, **84**, 5351; c) L. Zhou, Y. H. Lin, Z. Z. Huang, J. S. Ren and X. G. Qu, *Chem. Commun.*, 2012, **48**, 1147.
 - 17 a) P. C. Hsu, Z. Y. Shih, C. H. Lee and H. T. Chang, *Green Chem.*, 2012, **14**, 917; b) X. F. Jia, J. Li and E. K. Wang, *Nanoscale*, 2012, **4**, 5572; c) W. B. Shi, Q. L. Wang, Y. J. Long, Z. L. Cheng, S. H. Chen, H. Z. Zheng and Y. M. Huang, *Chem. Commun.*, 2011, **47**, 6695.
 - 18 a) J. M. Liu, J. T. Chen, and X. P. Yan, *Anal. Chem.*, 2013, **85**, 3238; b) P. K. Jain, X. H. Huang, I. H. El-Sayed, M. A. El-Sayed, *Acc. Chem. Res.*, 2008, **41**, 1578; c) C. W. Chen, C. H. Wang, C. M. Wei, C. Y. Hsieh, Y. T. Chen, Y. F. Chen, C. W. Lai, C. L. Liu and C. C. Hsieh, P. T. Chou, *J. Phys. Chem. C.*, 2009, **114**, 799; d) D. Cheng, W. Y. Han, K. C. Yang, Y. Song, M. D. Jiang, E. Q. Song, *Talanta*, 2014, **130**, 408.
 - 19 E. Q. Song, J. R. Li, H. Wei and Y. Song, *Anal. Methods*, 2012, **4**, 1199.
 - 20 a) R. E. Bailey and S. Nie, *J. Am. Chem. Soc.*, 2003, **125**, 7100; b) R. Demir-Cakan, N. Baccile, M. Antonietti and M. M. Titirici, *Chem. Mater.*, 2009, **21**, 484.
 - 21 a) S. Chandra, P. Das, S. Bag and D. Laha, *Nanoscale*, 2011, **3**, 1533; b) X. H. Wang, K. G. Qu, B. L. Xu, J. S. Ren and X. G. Qu, *J. Mater. Chem.*, 2011, **21**, 2445.
 - 22 a) C. P. Huang, Y. K. Li and T. M. Chen, *Biosens. Bioelectron.*, 2007, **22**, 1835; b) Angel Orte, Jose M. Alvarez-Pez, and Maria J. Ruedas-Rama, *ACS Nano*, 2013, **7**, 6387; c) Allison M. Dennis, Won Jong Rhee, David Sotto, Steven N. Dublin, and Gang Bao, *ACS Nano*, 2012, **6**, 2917.
 - 23 a) Y. F. Chen and Z. Rosenzweig, *Anal. Chem.*, 2002, **74**, 5132; b) S. Huang, Q. Xiao, R. Li, H. L. Guan, J. Liu, X. R. Liu, Z. K. He and Y. Liu, *Anal. Chim. Acta*, 2009, **645**, 73.
 - 24 a) C. Carrillo-Carrión, S. Cárdenas, B. M. Simonet, and M. Valcárcel, *Anal. Chem.*, 2009, **81**, 4730; b) W. Tedsana, T. Tuntulani, W. Ngeontae, *Anal. Chim. Acta*, 2013, **783**, 65.
 - 25 a) J. M. Liu, J. T. Chen and X. P. Yan, *Anal. Chem.*, 2013, **85**, 3238; b) M. C. Daniel, D. Astruc, *Chem. Rev.*, 2004, **104**, 293.